

MONTROSEITE, A NEW VANADIUM OXIDE FROM THE COLORADO PLATEAUS*

ALICE D. WEEKS, EVELYN A. CISNEY, AND ALEXANDER M. SHERWOOD
U. S. Geological Survey, Washington, D. C.

ABSTRACT

Montroseite, a new vanadium mineral named from Montrose County, Colo., has been found in four mines in western Colorado and in two mines in eastern Utah. It is black, opaque, submetallic, and occurs in microscopic bladed crystals of the orthorhombic dipyrarnidal class. The axial ratio is $a:b:c=0.509:1:0.310$, the common forms are b {010}, m {110}, p {121}, and a large vicinal form is approximately {0, 10, 1}. The observed specific gravity is 4.0, and the calculated specific gravity is 4.15. The composition is essentially VO(OH), with some iron commonly substituted for vanadium. Partial oxidation to VO₂ has taken place. Chemical analyses and x -ray diffraction data are given. Single crystal study indicated that the space group symmetry is $Pbnm(D_{2h}^{16})$.

INTRODUCTION AND ACKNOWLEDGMENTS

Montroseite was first collected by L. R. Stieff, T. W. Stern, and M. N. Girhard, of the U. S. Geological Survey, during the summer of 1949 at the Bitter Creek mine, Montrose County, Colo., and was studied by the writers in 1950. More montroseite was collected by A. D. Weeks from the Jo Dandy mine, Montrose County, and the Matchless mine, Mesa County, Colo., in 1950; from the Bitter Creek and the Whitney mines, Montrose County, Colo., in 1951, and from the Juniper mine, Grand County, Utah, in 1952. It was collected from the Rex No. 2 mine at Temple Mountain, Emery County, Utah, in 1952 by A. Rosenzweig of the Atomic Energy Commission.

The mineral was named after preliminary morphologic and x -ray study and chemical analysis had showed it to be different from any known vanadium mineral (Weeks, Cisney, and Sherwood, 1950). It was not fully described at that time because of the problem of a satisfactory chemical formula. The small unit cell determined by x -ray study indicated a simpler formula than was obtained from the chemical analysis.

Thanks are extended to L. R. Stieff, T. W. Stern, and M. N. Girhard, who collected the first sample; H. T. Evans and Stanley Block, of the Geological Survey, who determined the crystal structure and the correct chemical formula; also George Switzer, of the U. S. National Museum, who furnished material for comparison with the new mineral.

This work was done on behalf of the Division of Raw Materials of the U. S. Atomic Energy Commission.

* Publication authorized by the Director, U. S. Geological Survey.

OCCURRENCE

Four of the mines in which montroseite has been recognized are located in the Uravan mineral belt (Fischer and Hilpert, 1952) in western Colorado. The fifth locality, the Juniper mine, near Thompsons, Utah, is along a possible northwest extension of the Uravan belt. These five mines are in the Salt Wash sandstone member of the Morrison formation (Late Jurassic). The sixth locality is the Rex No. 2 mine in Shinarump conglomerate (Triassic) at Temple Mountain on the southeast side of the San Rafael swell in Utah. (See Fig. 1.)

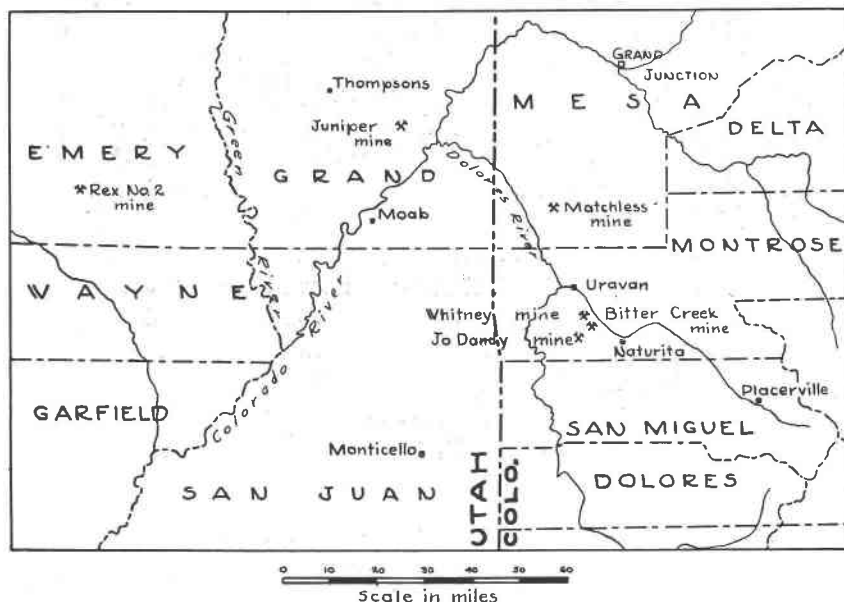


FIG. 1. Index map of localities of montroseite.

Montroseite occurs in black, relatively unoxidized vanadium-uranium ore; it is more abundant in the predominantly blacker ore at the Bitter Creek and the Whitney mines than at the Jo Dandy mine where the ore is generally oxidized and consists of minerals such as carnotite, hewettite, and hummerite. A small amount of pitchblende found at the Juniper and the Rex No. 2 mines is further indication of the relatively unoxidized environment of montroseite.

At the Bitter Creek and Whitney mines montroseite is the chief vanadium ore mineral in the blackest ore but is less abundant than corvusite in the greenish-black or blue-black ore. At the Matchless mine a small amount of montroseite was found in a band of corvusite ore with

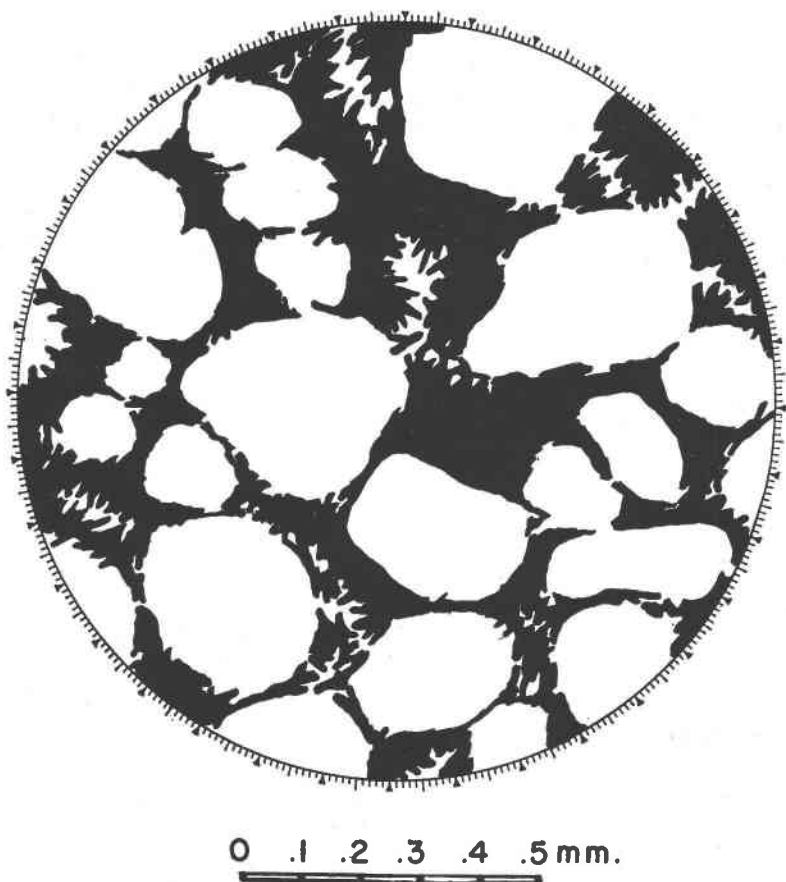


FIG. 2. Drawing of montroseite in thin section of ore sandstone from the Matchless mine, Mesa County, Colo.

thin seam fillings of hewettite. The montroseite is in microscopic crystals interstitial to the quartz grains of the ore-bearing sandstone (Fig. 2). The occurrence at the Jo Dandy mine may represent a further development of the situation at the Matchless mine; at Jo Dandy there is a very small amount of montroseite in dark patches of corvusite ore. At the Juniper mine a specimen of mineralized fossil bone was found to have microscopic tubelike fillings of montroseite in brown apatite.

A. Rosenzweig, of the Atomic Energy Commission, sent a few milligrams of nearly pure montroseite from the Rex No. 2 mine to the writers for identification. The sample consisted of cleavage fragments and aggregates of grains larger than those in other samples, and was the only

specimen suitable for measurement of specific gravity on a Berman balance.

PHYSICAL PROPERTIES

Montroseite is black, opaque, with submetallic luster and black streak. It forms microscopic crystals randomly oriented in massive ore, filling interstices between quartz sand grains, or filling small tubelike openings in fossil bone. Only the samples from the Bitter Creek mine contained single crystals large enough for goniometric and x -ray single crystal study. These bladed crystals, of the orthorhombic dipyramidal class, are commonly attached at one end and terminated with dome and pyramid faces on the other end. The crystals have good cleavage parallel to the length of the blade, $\{010\}$ and $\{110\}$, and are brittle. Superficially montroseite resembles melanovanadite in that both form elongated black crystals; but montroseite is orthorhombic and opaque, whereas melanovanadite is triclinic and strongly pleochroic in black and red. From the unit cell dimensions and chemical formula, the specific gravity of montroseite is calculated to be 4.15. The only specimen suitable for measurement of specific gravity, from the Rex No. 2 Mine, Emery County, Utah, gave 4.0. Montroseite can be separated or concentrated from the minerals with which it occurs by the use of methylene iodide and by the Frantz isodynamic separator because it is heavy and more magnetic than the associated minerals.

Goniometric measurements made on several crystals were inaccurate because of poor reflections, small faces, and multiple growth of crystals. They only served to determine the forms present, and the angle table (Table 1) has been computed from the unit cell lengths found by x -ray diffraction. The bladed crystals (Fig. 3) consist chiefly of the brachypinacoid and a steep brachydome, both with rough surfaces. The ρ angle of $p\{121\}$ could be determined better by finding a small circle including some reflection from the four small faces than by measuring each face

TABLE 1. ANGLES OF MONTROSEITE CRYSTAL

Orthorhombic; dipyramidal, $2/m\ 2/m\ 2/m$

$a:b:c=0.509:1:0.310$

$q_1:r_1:p_1=0.509:1.645:1$

$p_0:q_0:r_0=0.608:0.310:1$

$r_2:p_2:q_2=3.226:1.961:1$

Forms	ϕ	$\rho=c$	ϕ_1	$\rho_1=A$	ϕ_2	$\rho_2=B$
$b\ 010$	0°00'	90°00'	90°00'	90°00'	—	0°00'
$m\ 110$	62°59'	90°00'	90°00'	27°01'	0°00'	62°59'
$p\ 121$	44°26'	40°58'	31°48'	62°41'	58°42'	62°05'
Uncertain form						
$d\ 0, 10, 1$	0:00'	72°07'	72°07'	90°00'	90°00'	17°53'

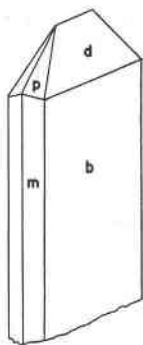


FIG. 3. Drawing of montroseite crystal.

individually, and the angle thus found was between $40^{\circ} 31'$ and 41° , in good agreement with the calculated angle.

X-RAY DIFFRACTION DATA

The *x*-ray powder pattern distinguishes montroseite from the other black vanadium minerals: melanovanadite, corvusite, and vanoxite (considered a doubtful species by the writers). Morphologic study indicated that montroseite belongs to the orthorhombic system, and this was borne out by *x*-ray study. Rotation and Weissenberg photographs taken around the *c* and *a* axes were poor and did not give sharp reflections, but the extinctions indicated the space group to be *Pbnm* (D_{2h}^{16}). From approximate measurements on the Weissenberg photographs the powder pattern was indexed (Table 2); the unit cell lengths were recalculated from measurements on the powder pattern. The unit cell lengths, $a_0 = 4.82$, $b_0 = 9.48$, and $c_0 = 2.93$, obtained in this way agree more closely with the diffuse lattices than with the sharp lattice of Evans and Block (1953). This is probably because the sample used for the powder pattern was considerably altered to VO_2 , whereas the single crystals contained a well-crystallized portion of the original $\text{VO}(\text{OH})$.

CHEMICAL ANALYSES

Montroseite presented a problem in chemical analysis because the vanadium is commonly in two valences and some iron substitutes for vanadium. A portion of the sample was digested in H_2SO_4 in the absence of air and was titrated with $\text{K}_2\text{Cr}_2\text{O}_7$. In this titration V_2O_3 is oxidized to V_2O_4 , and FeO to Fe_2O_3 . A second portion was digested in the same manner and was titrated with KMnO_4 . In this titration V_2O_3 is oxidized to V_2O_5 , V_2O_4 to V_2O_5 , and FeO to Fe_2O_3 . Total V and Fe were determined on separate portions. The analyses (Table 3) were computed from

TABLE 2. X-RAY DIFFRACTION POWDER PATTERN OF MONTROSEITE.
CuK α RADIATION

<i>hkl</i>	<i>d</i> (calc) Å	<i>d</i> (meas) Å	I
020	4.74	4.75	VF
110	4.30	4.31	S
120	3.38	3.38	M
130	2.643	2.644	S
101	2.507		
021	2.495	2.495	M
111	2.424	2.423	W
121	2.216	2.217	M
220	2.149	2.151	F
131	1.963	1.965	W
230	1.917	1.918	W
041	1.843	1.841	Fb
221	1.734	1.731	W
241	1.690	1.689	W
321	1.605	1.605	W
151	1.512	1.512	M
250	1.491	1.490	W
002	1.467	1.467	W
061	1.391	1.391	W
112	1.388		
170	1.304	1.302	F
132	1.283	1.282	F

these determinations: Total FeO and V₂O₃, total reducing ability of the mineral, total V, and total Fe.

The chemical analyses may be interpreted in the light of information obtained by *x*-ray structure study (Evans and Block, 1953). Ideally the original composition of montroseite was VO(OH), but the substitution of FeO requires an equivalent amount of V₂O₄. In the chemical analyses, the amount of V₂O₄ in excess of that required to balance the FeO represents the oxidation of the original mineral. The amount of water decreases as VO(OH) alters to VO₂. Calculation of the analysis (Table 3, column 3) of the sample from the Matchless mine, indicates about 35 per cent of [(Fe⁺²·V⁺⁴),V⁺³]O(OH) and about 65 per cent of VO₂.

None of the montroseite samples could be separated completely from the associated minerals, chiefly because montroseite occurs in such fine-grained mixtures. The sample (Table 3, column 2) from the Bitter Creek mine (120 mg.) was a loose aggregate of crystals and probably the purest of the three analyzed samples. The sample from the Matchless mine (Table 3, column 3) contained microscopic grains of montroseite between quartz grains and is only about 90 per cent pure. The sample (about 12 g)

TABLE 3. CHEMICAL ANALYSES OF MONTROSEITE (IN PER CENT)

Analyst: A. M. Sherwood, U. S. Geological Survey

	1	2	3	4
V ₂ O ₃	89.29	10.5	11.10	
V ₂ O ₄		72.5	66.90	69.35
V ₂ O ₅				0.48
FeO		8.8	8.26	
Fe ₂ O ₃				10.33
H ₂ O	10.71	5.0	4.82	10.60
SiO ₂			6.12	3.56
Al ₂ O ₃			3.00	1.87
UO ₃				2.60
MgO				0.56
CaO				0.24
S				0.09
Total	100.0	96.8	100.20	99.68

1. HVO₂ or V₂O₃·H₂O.
2. Partial analysis on a 120-mg sample from Bitter Creek mine.
3. Matchless mine.
4. Whitney mine.

from the Whitney mine (Table 3, column 4) is not more than 85 per cent pure and contains clay, possibly corvusite and a new black uranium mineral, and a little pyrite.

PARAGENESIS

Montroseite is the least oxidized vanadium mineral thus far found in the Colorado Plateaus uranium-vanadium ores and it is thought to be a primary mineral. It occurs with or in the same environment as pitchblende and a new black uranium mineral not yet described, as well as with pyrite, galena, and other sulfides. In the zone of oxidation it is altered to corvusite, melanovanadite, and the quinquevalent vanadium minerals hewettite, pascoite, and hummerite.

REFERENCES

- EVANS, H. T., AND BLOCK, S. (1953), The crystal structure of montroseite, a new vanadium member of the diasporite group: *Am. Mineral.*, **38**, 1242-1250.
- FISCHER, R. P., AND HILPERT, L. S. (1952), Geology of the UraVan mineral belt: *U. S. Geol. Survey Bull.* **988-A**, 13 pp.
- WEEKS, A. D., CISNEY, E. A., AND SHERWOOD, A. M. (1950), Hummerite and montroseite, two new vanadium minerals from Montrose County, Colorado: *Geol. Soc. America Bull.*, **61**, 1513 (abstract).