

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

2

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) An Improvement to Low-Level Radioactive Waste Vitrification Processes		5. TYPE OF REPORT & PERIOD COVERED
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) MAJ Walter S. Horton		8. CONTRACT OR GRANT NUMBER(s)
9. PERFORMING ORGANIZATION NAME AND ADDRESS Student 200 Stoval St. HODA, MILPERCEN Alexandria, VA, 22332 ATTN: DAPC-OPA-E		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS
11. CONTROLLING OFFICE NAME AND ADDRESS		12. REPORT DATE May 86
		13. NUMBER OF PAGES 70
MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
DISTRIBUTION STATEMENT (of this Report) Approved for public release, distribution unlimited.		
DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
16. SUPPLEMENTARY NOTES M.S. Thesis, University of Illinois, Urbana, IL		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Low-Level Waste, Low-Level Radioactive Waste, Vitrification, Cesium, Cs-137, Waste Economics, Ion Exchange, Electrodialysis, Zeolites, 10 CFR 61, Shallow Land Burial, Cementation, Bituminization, Waste Immobilization, Chemical Precipitation		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Low-Level Radioactive Waste Vitrification (LLWV) is a technically feasible and cost competitive alternative to the traditional immobilization options, i.e., cementation or bituminization. This thesis analyzes cementation, bituminization and vitrification, reviews the impact of the Low-Level Waste stream composition on the vitrification process, then proposes and discusses several techniques to control the volatile radionuclides in a Process Improved LLWV system (PILLWV). The techniques that control the volatile radionuclides include chemical precipitation, electrodialysis, and ion exchange. Ion exchange is preferred. A com-		

DTIC ELECTE
AUG 21 1986
S A

AD-A171 146

DTIC FILE COPY

86-8-21-085

Block 20 Contd.

parison of the technical specifications, of the regulatory compliance, and of the cost considerations shows the PILLWV to be the superior LLW immobilization option.

An Improvement to Low-Level Radioactive Waste Vitrification Processes

**Walter S. Horton, MAJ
HQDA, MILPERCEN (DAPC-OPA-E)
200 Stoval Street
Alexandria, VA 22332**

May 86

Approved for public release, distribution unlimited.

**A thesis submitted to the University of Illinois, Urbana , IL in partial fulfillment
of the requirements for the degree of Master of Science in Nuclear Engineering.**



Handwritten marks and a stamp in the bottom right corner. A large checkmark is visible in the upper right. Below it, there is a stamp that reads "DTIC" and "COPY INSPECTED". To the right of the stamp, there are handwritten initials "A1" and a vertical line.

**AN IMPROVEMENT
TO
LOW-LEVEL RADIOACTIVE WASTE
VITRIFICATION PROCESSES**

BY

WALTER SAN HORTON

B.S., Clemson University, 1973

Thesis

**Submitted in partial fulfillment of the requirements
for the degree of Master of Science in Nuclear Engineering
in the Graduate College of the
University of Illinois at Urbana-Champaign, 1986**

Urbana, Illinois

UNIVERSITY OF ILLINOIS AT URBANA-CHAMPAIGN

THE GRADUATE COLLEGE

April, 1985

WE HEREBY RECOMMEND THAT THE THESIS BY
WALTER SAN HORTON

ENTITLED AN IMPROVEMENT TO LOW-LEVEL RADIOACTIVE
WASTE VITRIFICATION PROCESSES

BE ACCEPTED IN PARTIAL FULFILLMENT OF THE REQUIREMENTS FOR
MASTER OF SCIENCE
THE DEGREE OF _____

Alderrafi M. Dugouag Director of Thesis Research
Berkeley G. Jones Head of Department

Committee on Final Examination†

Chairperson
James H. Stubbs

† Required for doctor's degree but not for master's.

ACKNOWLEDGEMENT

The author wishes to thank his advisor, Professor A.M. Ougouag, for his guidance, encouragement, assistance, and many valuable suggestions during the course of this work. Professor Ougouag is more than an advisor, he is a trusted friend who helped me adjust to the rigors of academic life.

The author also wishes to thank Professor Emeritus Daniel F. Hang for his valuable discussion concerning the economic aspects of this thesis and helpful remarks about this work.

The author wishes to thank Professor James F. Stubbins for his interest, his valuable comments, and for accepting to be a member of the committee for this thesis.

The friendship and encouragement of the author's classmates John B. O. Caughman, III, George M. Hrbek, Jyi-yu Sun, Gregory J. Hutchens, John Mandrekas, and especially Chin Pan, made studying and learning an enjoyable experience and are gratefully acknowledged.

Last, but certainly not least, the author acknowledges the loving patience and understanding his wife, Barbara, for enduring my long absences from home during this tour of duty.

TABLE OF CONTENTS

Chapter		Page
1	INTRODUCTION	1
	1.1 Introduction	1
	1.2 Scope of this Thesis	2
	1.3 Terminology Review	2
2	LLW IMMOBILIZATION OPTIONS ANALYSIS	6
	2.1 Introduction	6
	2.2 Traditional Immobilization Methods Assessment	6
	2.3 LLWV Immobilization Assessment	9
	2.4 LLW Stream Composition Impact on LLWV	9
	2.4.1 LLW Stream Composition	13
	2.4.2 LLWV Safety Assessment	14
	2.4.3 Cesium Test Facility Effects	15
	2.5 Conclusion	15
3	PROCESS IMPROVED LLWV	17
	3.1 Introduction	17
	3.2 Ion Exchange	17
	3.3 Chemical Precipitation	23
	3.4 Electrodialysis	24
	3.5 Conclusion	27

Chapter	Page
4	PILLWV REGULATORY COMPLIANCE AND COST ESTIMATION29
4.1	Introduction29
4.2	Regulatory Compliance33
4.3	Cost Estimation36
4.4	Conclusion40
5	SUMMARY AND RECOMMENDATIONS FOR FURTHER STUDY42
5.1	Summary of Results42
5.2	Recommendations for Future Study44
APPENDIX	
A	LLW DISPOSAL RATE SCHEDULES46
B	LWR WASTE STREAM CHARACTERISTICS55
	REFERENCES58
	VITA63

LIST OF ABBREVIATIONS

AEIC	Annual Equivalent Installation Cost
AIOC	Annual Installation and Operation Cost
AGD	Above Ground Disposal
A_e	Activity of Effluent
A_i	Activity of Influent
BWR	Boiling Water Reactor
CFR	Code of Federal Regulations
Ci	Curie
Conc	Concentration
DBA	Design Basis Accident
DF	Decontamination Factor
DOE	United States Department of the Energy
DOT	United States Department of Transportation
DWPF	Defense Waste Processing Facility
E-1	$1 \times 10^{-1} = 0.1$
EIE	Electrodialysis-Ion Exchange
EPA	United States Environmental Protection Agency
ELECD	Electrodialysis
ESLB	Enhanced Shallow Land Burial
ft^3	Cubic Foot
HLW	High Level Waste
hr	Hour

IAEA	International Atomic Energy Agency
L	Liter
LLWV	Low-Level Waste Vitrification
LWR	Light Water Reactor
m ³	Cubic Meter
mrem	Millirem
MWe	Mega Watt Electric
nCi	NanoCurie
NRC	United States Nuclear Regulatory Commission
PILLWV	Process Improved Low-Level Waste Vitrification
PVC	Polyvinyl Chloride
PWR	Pressurized Water Reactor
rem	Unit Dose Equivalent in cgs system
SLB	Shallow Land Burial
Soln	Solution
TMI	Three Mile Island
VR	Volume Reduction

CHAPTER 1
INTRODUCTION

1.1 Introduction

The operation of nuclear reactors generates radioactive wastes that require effective, and economical immobilization and disposal.

The traditional Low-Level Radioactive Waste (LLW) immobilization options are cementation or bituminization. Either of these options could be followed by Shallow Land Burial (SLB) or Above Ground Disposal. These rather simple LLW procedures appeared to be readily available, to meet regulatory requirements, and to satisfy cost constraints. The authorization of State Compacts, the forced closure of half of the six SLB disposal facilities of the U.S., and the escalation of transportation/disposal fees diminish the viability of these immobilization options. The synergetic combination of these factors led to a reassessment of traditional methods and to an investigation of other techniques. Low Level Radioactive Waste Vitrification (LLWV) is a technically feasible, and cost competitive alternative to the existing LLW immobilization options.¹ This thesis proposes several techniques to control the volatile radionuclides in LLW.

1.2 Scope of this Thesis

The purpose of this thesis is to analyze the traditional LLW immobilization options, to review the impact of the LLW stream composition on LLWV, then to propose and discuss several techniques to control the volatile radionuclides in a Process Improved LLWV system (PILLWV). This chapter contains the introduction and background information. The background section of this chapter clarifies for the reader the radioactive waste management terminology. Chapter 2 analyzes the most common LLW immobilization options. The next chapter proposes several improvements to the LLWV process which is described in Ref.1. These improvements are applications of existing technology to the LLWV system and are aimed at controlling the volatile radionuclides. Chapter 4 illustrates the regulatory compliance of the PILLWV waste form and provides a cost estimation of an ion exchange PILLWV. The final chapter summarizes the thesis results and presents recommendations for further work. The general results of chapter 3 and chapter 4 were presented at the Waste Management '86 conference and are to be published.²

1.3 Terminology Review

The terminology of the Radioactive Waste Management is both dynamic and confusing even for an expert. This dismal state of affairs results from the lack of a single

controlling agency that is responsible for terminology standardization, and from the interdisciplinary nature of Radioactive Waste Management. This section reviews and clarifies the currently accepted terminology.

Radioactive Wastes³ (Radwaste) is:

the generic term for gases, liquids, solids, and equipment produced or used in nuclear operations of negligible economic value that contain radionuclides in excess of threshold quantities except for radioactive material from post weapons test activities.

In the U.S. Radwaste is subdivided into three categories: High-level Radioactive Wastes (HLW), Transuranic Radioactive Wastes (TRU), and Low-Level Radioactive Wastes (LLW). The Nuclear Regulatory Commission defines^{4,5} HLW as:

(1) Irradiated reactor fuel, (2) liquid wastes resulting from the first-cycle solvent extraction system, or equivalent, and the concentrated wastes from subsequent extraction cycles, or equivalent, in a facility for reprocessing irradiated reactor fuel, and (3) solids into which liquid wastes have been converted.

TRU's were originally defined as those wastes contaminated with U-233 or transuranic radionuclides. This was changed when 10 CFR 61 was adopted. The currently accepted definition⁶ of TRU waste is:

material of no economic value which at the end of the institutional control periods contains alpha emitters of atomic number greater than 92 (but including U-233), with half-lives of greater than 20 years and in concentrations greater than 100 nCi/g.

Finally, LLW is defined⁷ as:

radioactive wastes not classified as HLW, TRU, spent fuel, or by-product material as defined in section 11e.(2) of the Atomic Energy Act (uranium or thorium mill tailings and waste).

This broad definition of LLW includes wastes which vary greatly in radionuclide content, in physical and chemical form, and/or in specific activity.

Various Federal and State regulations prescribe the maximum Radwaste concentrations that are safe to release to the environment. Waste concentrations above these maxima require immobilization prior to disposal. Here, immobilization means the conditioning processes that yield a waste form which minimizes the migration or leaching of the Radwaste. Disposal is defined⁸ as

the isolation of radioactive wastes from the biosphere inhabited by man and containing his food chains by emplacement in a land disposal facility.

Various Radwaste immobilization and disposal schemes are used or are in development (Table 1.1).

TABLE 1.1

Radwaste Immobilization and Disposal Schemes

<u>Waste</u>	<u>Immobilization Form</u>	<u>Disposal Technique</u>
HLW	Clays Concretes Calcines Glasses Crystalline Ceramics	Geologic Burial
LLW	Urea-formaldehyde Cement Bitumen (asphalt) Glass	Above Ground Enhanced Shallow Land Burial Shallow Land Burial
TRU	All of the Above (Activity Dictated)	All of the Above

Geologic Burial means disposal of Radwaste in an excavated geologic formation⁹, whereas Shallow Land Burial (SLB) is Radwaste disposal in or within the upper 30 meters of the earth's surface.¹⁰ Above Ground Disposal (AGD) is as its name implies Radwaste disposal in a structure above the earth's surface. Enhanced Shallow Land Burial (ESLB) is SLB that has been improved by incorporating engineered confinement schemes.¹¹

The last term that the reader should be familiar with is the Decontamination Factor (DF). The DF is an efficiency figure of merit for processes (filters, ion exchange columns, etc.) that partition or decontaminate Radwaste streams.¹²

CHAPTER 2

LLW IMMOBILIZATION OPTIONS ANALYSIS

2.1 Introduction

The traditional LLW immobilization techniques include cementation and bituminization. Cementation incorporates the LLW into a cement matrix, while bituminization encapsulates the LLW with bitumen (asphalt). The proposed HLW immobilization process in the U.S., vitrification, incorporates the Radwaste into a glass matrix. This process is technically complex and expensive, and it initially received little consideration as an LLW immobilization alternative.

2.2 Traditional Immobilization Methods Assessment

Cementation and bituminization have been reported to present serious technical and economic disadvantages. Technical disadvantages of cementation include low waste loading, high cesium and sodium leachability, and the inherent volume increase of the waste form.^{1,13} In this thesis, waste loading means the percent concentration of the radwaste in the waste form, rather than the percent of radionuclides or the percent of fission products in the waste.¹⁴ Leaching refers to the degradation of the chemical durability of waste forms by the resultant, overall chemical reaction between radioactive waste forms and water.¹⁵ Table

2.1 summarizes waste loadings and leachabilities of cement and glass, and shows the immobilization advantage of glass.

TABLE 2.1

Comparison of Waste Loading and Leachability^{13*}

<u>Waste Form</u>	<u>Waste Loading(%)</u>	<u>Cesium Leaching(%)</u>
Cement	10 to 5	47.5
Glass	<u>33</u>	<u>0.1</u>
Glass Increase(Decrease)	3 to 6 times	(475) times

* Reference 13 does not specify the glass advantage.

Cement is incapable of immobilizing cesium without additional processing. Zeolite absorption schemes are used to minimize the cesium leaching in cement at defense waste treatment facilities.¹⁶

Bituminization, which is used extensively outside the U.S., yields a waste form that is flammable¹ and very leachable.¹⁷ Reference 17 explicitly states that bituminization is ill-advised for immobilization of cesium. Table 2.2 summarizes the results of Ref. 17.

TABLE 2.2

Bitumen Immobilization Constraints¹⁷

- * Cesium insolubilization
- * No metals, glass, rubbish, filters, PVC
- * No solvents with Boiling Points $\leq 140^{\circ}\text{C}$
- * Water content $\leq 5\%$

Finally, disposal fees at the three operating SLB sites have escalated by up to 300% since 1983.^{18,19} Appendix A provides the 1983 and the 1985 commercial LLW disposal rate schedules for the three SLB sites. For illustrative purposes, Table 2.3 shows the curie surcharge rate increase at Barnwell, S. C. from 1983 to 1985.

TABLE 2.3

Comparison of Curie Surcharge Fees
(Barnwell, SC)

Content per Shipment (Ci)	1985 Surcharge ¹⁸ (\$)	1983 Surcharge ¹⁹ (\$)	Increase (%)
1.2-5	1500	500	300
75.1-100	7450	2500	298
250-500	15000	5000	300
1000.1-5000	24000	8000	300

These technical and economic problems warrant the search for an alternative to the traditional LLW immobilization options.

2.3 LLWV Immobilization Assessment

Reference 1 describes in detail a proposed LLWV process which is summarized in Fig. 1.1. Vitrification produces smaller waste volumes.¹ This advantage is a significant factor for SLB, ESLB, and/or AGD, when one considers available disposal space and disposal costs that are based upon waste volumes. Vitrification also produces a waste form with leaching resistance¹³ superior to the previously reviewed methods (Table 2.1). The LLWV waste form was shown to be in compliance with the proposed regulation 10 CFR 61.¹ Since the publication of Ref.1., 10 CFR 61 was approved, and an updated assessment of the regulatory compliance of the LLWV waste form is provided in Table 2.4. Reference 1 also shows that the process is cost competitive with the traditional LLW immobilization options (Table 2.5).

2.4 LLW Stream Composition Impact on LLWV

The glass waste form of the vitrification process is produced by heating the Radwaste and glass formers to approximately 1150-1500°C. This high temperature heat treatment requires modifications to control the volatile radionuclides of LLW streams.

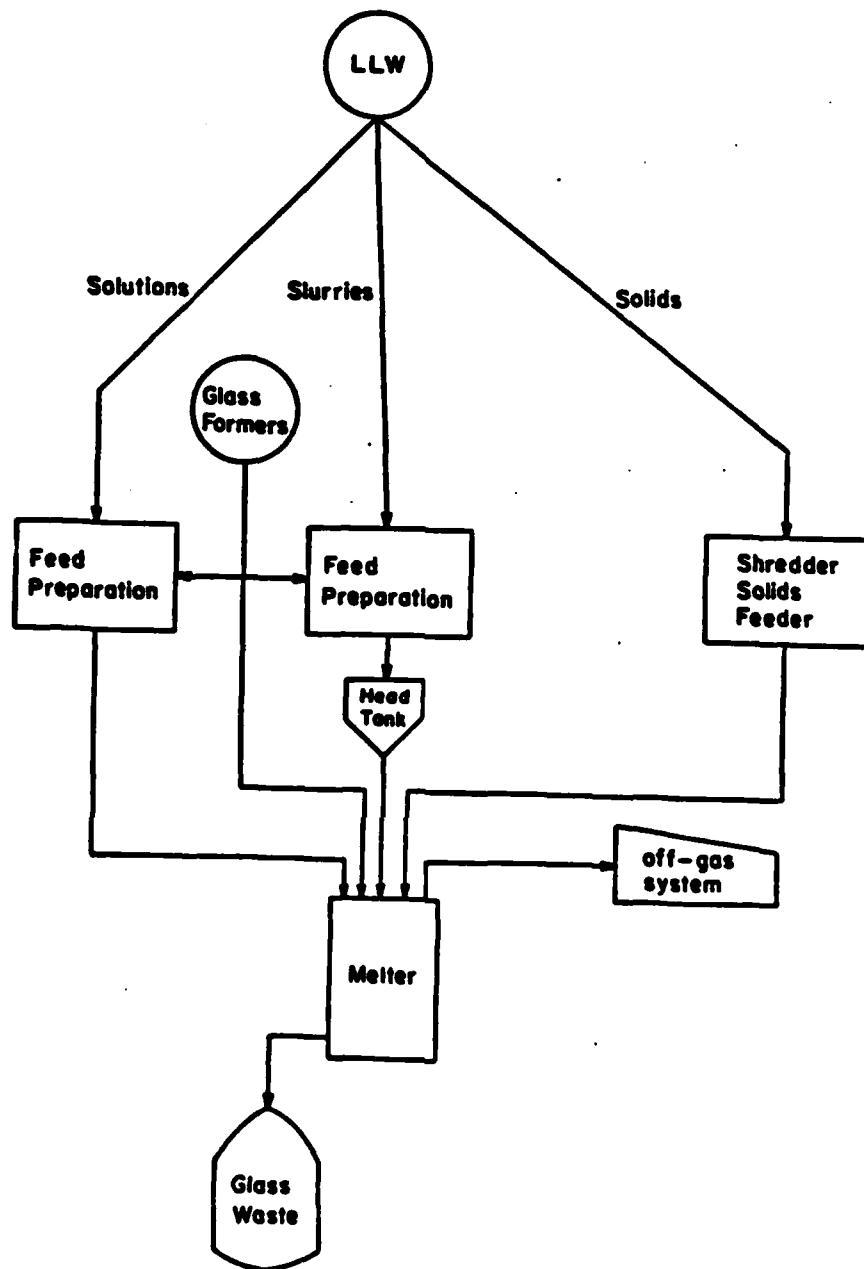


Fig. 1.1. Proposed LLW Process¹

TABLE 2.4
FEDERAL REGULATIONS COMPLIANCE

19 CFR 61 Part 61.36: Waste Characteristics	Properties of Waste Glass
<p>(a) The following requirements are minimum requirements for all classes of waste and are intended to facilitate handling at the disposal site and provide protection of health and safety of personnel at the disposal site.</p> <p>(1) Wastes must not be packaged for disposal in cardboard or fiber board boxes.</p> <p>(2) Liquid waste must be solidified or packaged in sufficient absorbent material to absorb twice the volume of the liquid.</p> <p>(3) Solid waste containing liquid shall contain as little free standing and noncorrosive liquid as is reasonably achievable, but in no case shall the liquid exceed 1% of the volume.</p> <p>(4) Waste must not be readily capable of detonation or of explosive decomposition or reaction at normal pressures and temperatures, or of explosive reaction with water.</p> <p>(5) Waste must not contain, or be capable of generating quantities of toxic gases, vapors, or fumes harmful to persons transporting, handling, or disposing of the waste. This does not apply to radioactive gaseous waste packaged in accordance with paragraph (a)(7) of this section.</p> <p>(6) Wastes must not be pyrophoric. Pyrophoric materials contained in the wastes shall be treated, prepared, and packaged to be nonflammable.</p> <p>(7) Wastes in gaseous form must be packaged at a pressure that does not exceed 1.5 atmospheres at 20 degrees centigrade. Total activity must not exceed 100 curies per container.</p> <p>(8) Wastes containing biological, pathogenic, or infectious material must be treated to reduce to the maximum extent practicable the potential hazard from the nonradiological</p>	<p>(1) Waste glass is packaged in metal containers.</p> <p>(2) Waste glass processing eliminates any liquid water in the waste form.</p> <p>(3) Waste glass processing eliminates any liquid water in the waste form.</p> <p>(4) Waste is chemically stable because any chemically reactive wastes are stabilized in the glass forming process.</p> <p>(5) Waste is stable and does not generate toxic gases, vapors, or fumes.</p> <p>(6) Waste is not pyrophoric.</p> <p>(7) Does not apply.</p> <p>(8) These wastes are decomposed to nontoxic form by thermal degradation and oxidation in the glass forming process.</p>

TABLE 2.4
(CONTINUED)

10 CFR 61
Part 61.56: Waste Characteristics

Properties of Waste Glass

(b) The requirements in this section are intended to provide stability of the waste. Stability is intended to ensure that the waste does not structurally degrade and affect overall stability of the site through slumping, collapse, or other failure of the disposal unit and thereby lead to water infiltration. Stability is also a factor in limiting exposure to an inadvertent intruder, since it provides a recognizable and nondispersible waste.

(1) Waste must have structural stability. A structurally stable waste form will generally maintain its physical dimensions and its form, under the expected disposal conditions such as weight of overburden and compaction equipment, the presence of moisture, and microbial activity, and internal factors such as radiation effects and chemical changes. Structural stability can be provided by the waste form itself, processing the waste to a stable form, or placing the waste in a disposal container or structure that provides stability after disposal.

(2) Notwithstanding the provisions in Part 61.56(a)(2) and (3), liquid wastes, or wastes containing liquid, must be converted into a form that contains as little free-standing and non-corrosive liquid as is reasonably achievable, but in no case shall the liquid exceed 1% of the volume of the waste when the waste is in a disposal container designed to ensure stability, or 5% of the volume of the waste for waste processed to a stable form.

(3) Void spaces within the waste and between the waste and its package must be reduced to the extent practicable.

(1) (a) Waste glass expansion change with a 100 degree centigrade temperature change is 0.1%.

(b) Compressive strength of the waste glass is 6.9 to 140 MPa. (1 to 20 ksi)

(c) Waste glass is chemically, thermally, and radiolytically stable.

(2) Vitrification eliminates liquid water from the waste form.

(3) The waste glass product is a solid monolith within its container with the exception of some cracks in the glass structure.

TABLE 2.5
ANNUAL RADWASTE MANAGEMENT COSTS^{a1}
(1984 \$1000)

<u>Cost item</u>	<u>No Volume Reduction</u>	<u>Vitrifi- cation</u>	<u>Calcination/ Incineration</u>	<u>Bitumini- zation</u>	<u>Evaporator/ Crystallizer</u>	<u>Shredding/ Compaction</u>	<u>Incineration</u>
Total materials and burial	1,954	353	707	1,200	1,545	1,822	1,722
Solidification labor cost	535	37	102	128	354	535	549
WR operating cost	--	895	355	833	85	-44	229
WR amortized capital cost	--	500	902	712	203	7	289
Drum storage cost credit	--	-90	-84	-67	-27	-10	-17
Transportation to burial	<u>2,011</u>	<u>694</u>	<u>997</u>	<u>2,696</u>	<u>1,962</u>	<u>1,990</u>	<u>1,976</u>
Total	4,500	2,389	2,979	5,503	4,123	4,300	4,738

^aCase is for 1100-MWe BWR, 1250 miles transportation, Barnwell burial.

2.4.1 LLW Stream Composition

Reference 20 gives typical radionuclide compositions of LLW streams. Cesium is a predominant radionuclide in the LLW streams of Light Water Reactors.^{20,21} Appendix B shows the concentrations of radionuclides in these waste streams. Table 2.6 gives the relative content of cesium activity in each these LLW streams.

TABLE 2.6

LLW Radionuclide Composition			
<u>LLW Stream</u>	<u>Total²⁰ (Ci/MWe)</u>	<u>Cesium²⁰ (Ci/MWe)</u>	<u>Cesium (%)</u>
BWR	2.142	1.232	57.5
PWR	0.771	0.313	40.6

2.4.2 LLWV Safety Assessment

A Safety Assessment and Major Radionuclides in the Source Term were reported in Ref. 1. An analysis (Table 2.7) of this Safety Assessment shows that cesium is the major contributor to the source term for LLWV Design Basis Accidents (DBA).

TABLE 2.7

Source Term Analysis

<u>Design Basis Accident</u>	<u>% Cs in Source Term</u>
Glass Leakage	100
Thermal Shock Wave	100
Inoperative Scrubber	50
Venturi Leak	50
Full Container Drop	100
Cell Cover Dropped	50
Melter Pressurization	50
Plenum Leakage	50
Regeneration Solution Spill	50

2.4.3 Cesium Test Facility Effects

Predominance in the LWR LLW stream and in the DBA source term initially identified cesium as the radionuclide to be controlled. The need for cesium control is further supported by LLLWV pilot experiments.

LLWV test results at Mound Laboratory show that cesium is sorbed in the walls of the glass melter and in the components of the off-gas system. Furthermore, the cesium can be randomly desorbed. LLW streams of 1 mCi to 5.2 mCi of cesium were vitrified. It was found that between 11% and 28% of the cesium was unaccounted for.²²

Analysis of the experimental data reported in Ref. 22 shows significant cesium retention when ion exchange resins are vitrified. For a large number of experiments, the unaccounted cesium percentage, in average, for ion exchange resins is 12.5, whereas the unaccounted cesium percentage, in average, for dry solid wastes is 20.1.

The adsorption of cesium produces an unacceptable system mass balance.²² The sorption and random desorption of cesium would seriously hinder the licensing process of a commercial LLWV facility.

2.5 Conclusion

Waste Loading and leachability of the LLWV waste form is superior to both cementation and bituminization.¹⁰ Further, the LLWV glass exceeds all standards of stability

as prescribed in 10CFR61.¹ The escalation of SLB disposal fees requires the use of an immobilization process which optimizes volume reduction.

Cesium is shown to be the predominant radionuclide in LLW streams,²⁰ to be the principal source term in DBA's,¹ and to be randomly sorbed/desorbed by the melter and off-gas components during vitrification.²² The foregoing analysis identifies cesium as the critical volatile radionuclide that must be controlled in order to improve the proposed LLW processes. In the next chapters, process improvements are proposed and discussed.

CHAPTER 3

PROCESS IMPROVED LLWV

3.1 Introduction

The Process Improved LLWV (PILLWV) controls the volatility of cesium by selectively incorporating the radionuclide into a vitrifiable form. In essence, the initial LLW stream is partitioned prior to the feed preparation step of Fig. 1.1. Numerous processes that selectively separate and fix cesium are reported in the literature and are in various stages of development both in the U.S. and elsewhere. These processes include ion exchange,^{23,24} chemical precipitation,²⁵ and electro dialysis.²⁶ Each process in turn will be reviewed.

3.2 Ion Exchange

Ion exchange is a well developed industrial application and is currently used in the management of High-Level Wastes (HLW) at Defense Waste Processing Facilities.^{16,23,24} Adaptation of the ion exchange process to wastes other than HLW is novel in this country, but it has received moderate study in Sweden,²⁷ Japan,²⁸ and the USSR.^{29,30,31} The ion exchange process described in Ref. 27 transfers the activity of spent organic ion exchange resins to inorganic ion exchange media. Reference 28 reports fundamental data on cesium ion exchange with a hexacyanoferrate (II) impregnated zeolite. Soviet researchers (Refs. 29, 30, 31) recommend

decontamination of Low- and Medium-Level radioactive wastes by ion exchange prior to bituminization or cementation. These processes were meant to reduce the volume of the waste prior to immobilization by the traditional techniques.

An ion exchange process using heat resistant and cesium specific media will control cesium's volatility during vitrification. Recall from section 2.4.3 that the unaccounted cesium is less even when general purpose bead resins are vitrified. In Fig. 3.1 the conceptual design of a possible ion exchange PILLWV is shown.

A continuous ion exchange system is recommended due to its demonstrated efficiency and economy for nuclear³⁰ and non-nuclear³² applications (Table 3.1 and Table 3.2).

TABLE 3.1

ION EXCHANGE EFFICIENCY³⁰⁺

<u>ION EXCHANGE SYSTEM</u>	<u>Volume of Exchanger(L)</u>	<u>DF</u> ⁺
Continuous	30	700
Fixed	600	200

⁺ Decontamination Factor

Table 3.1 shows that continuous ion exchangers are 2.5 times more efficient and require 20 times less volume than fixed bed exchangers. In addition, Table 3.2 shows that

continuous ion exchangers are approximately 25% cheaper than fixed bed ion exchangers.

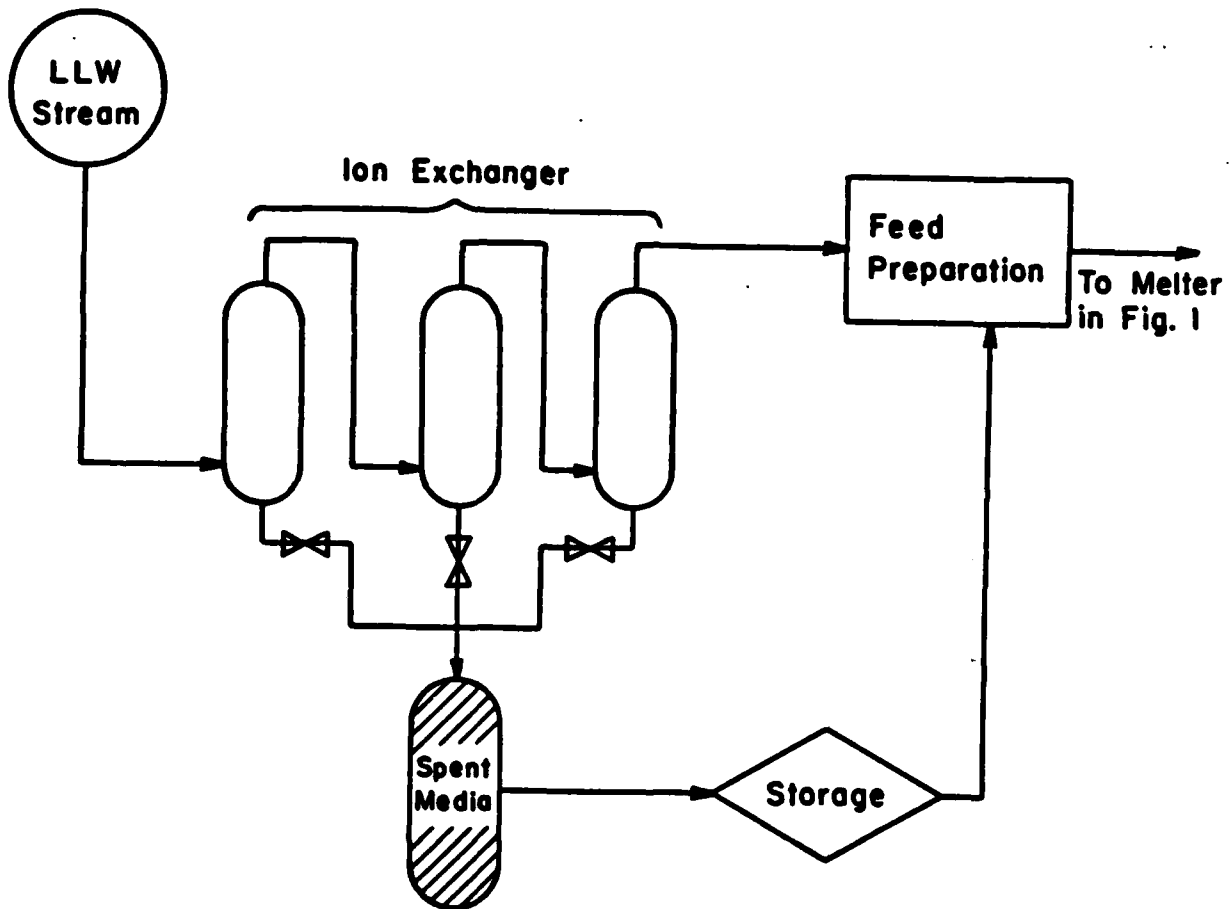


Fig. 3.1. Ion Exchange PILLOW

TABLE 3.2

Cost Comparison
Continuous Versus Fixed Bed Ion Exchange

<u>Type</u>	<u>Cost³²</u> <u>(\$1000)</u>	<u>Continuous Ion</u> <u>Exchange Advantage</u>
General		
Continuous	2164	
Fixed	2773	
		22%
Softening		
Continuous	206	
Fixed	284	
		27%
NaH BLEND		
Continuous	1038	
Fixed	1410	
		26%

The technical criteria used to determine the ion exchange media include high cesium selectivity, high radiation resistivity, and good thermal stability. The selection of the ion exchange medium should be tailored to a particular LLW stream, however several effective candidates are given in Table 3.3.

TABLE 3.3

Ion Exchange Media Candidates

<u>Medium</u>	<u>Waste Stream</u>	<u>DF⁺</u>
Duolite CS-100 ^{++33,34}	HLW	10000
Titanates ²⁷	HLW	10000
Duolite ARC-359 ⁺⁺¹⁶	HLW	10000
γ -Zirconium Phosphate ^{35,36}	TMI Accident	10000

⁺ Decontamination Factor

⁺⁺ Duolite CS-100 and Duolite ARC-359 are manufactured by Diamond Shamrock Corporation

All of the candidate media have high cesium selectivity and radiation resistance. In addition, these ion exchange media retain cesium during heat treatment which is a crucial requirement for vitrification. The first three media of Table 3.3 have been vitrified at HLW facilities, and γ -Zirconium Phosphate has successfully been sintered.^{33,27,35}

Preprocessing the LLWV stream with an ion exchange system provides a significant reduction of the amount of cesium in the melter feed (Table 3.4).

TABLE 3.4

	Melter Feed Cesium Concentration	
	<u>Untreated²⁰ Cs Concentration (1000 MWe-yr)</u>	<u>Predicted Cs Concentration</u>
BWR LLW	8.640E-1 Ci/m ³	8.64E-5 Ci/m ³
PWR LLW	4.074E-1 Ci/m ³	4.07E-5 Ci/m ³

The reduction, shown in Table 3.4, is calculated with the reported DF's of Table 3.3 and the Decontamination Factor (DF) formula³⁷, $DF = A_i / A_e$:

where

- DF = Decontamination Factor
- A_i = Influent Activity
- A_e = Effluent Activity

In summary, a continuous ion exchange treatment system uses fully developed and proven technology that could be easily integrated into the LLW process. An ion exchange PILLW effectively controls the volatility of cesium during vitrification and the partitioned waste stream may be also processed into a waste glass. The ion exchange PILLW capitalizes on the effectiveness of ion exchange and vitrification to produce a superior waste form in a superior LLW treatment system.

3.3 Chemical Precipitation

A chemical precipitation system would be integrated in the LLWV process in the same way as an ion exchange process (Fig. 2). This technique (precipitation) is used to remove cesium from low-level waste salts prior to cementation and disposal at the Defense Waste Processing Facility (DWPF) at the Savannah River Plant (SRP).²⁴ SRP has underground waste storage tanks containing large inventories of cesium in solution. Chemical precipitation of the cesium decontaminates these solutions and is easily integrated into SRP's existing process. While chemical precipitation has been adopted by SRP, it appears that the process is not as effective as anticipated.³⁸

West Valley also investigated chemical precipitation as a potential cesium removal and volume reduction process. The efficiency of chemical precipitation to remove cesium from the waste streams of West Valley was found to be lower than ion exchange. The unacceptably low efficiency for the precipitation process at West Valley is due to the difference in pH and radionuclide concentration of the waste stream.³⁹

Sodium and Potassium tetraphenyl borates are both cited in the literature as having high cesium selectivity.^{23,25,39} The thermal properties of the precipitates that they produce have not been reported. These properties must be established prior to vitrification. Furthermore, as seen

above the individual waste stream characteristics (pH of the solution, presence and/or concentration of competing ions) can greatly impact the effectiveness of a chemical precipitation system.

3.4 Electrodialysis

Reference 40 defines electrodialysis as a process in which a selectively permeable membrane separates a specific substance from a solution of numerous substances. Two other membrane processes are dialysis and reverse osmosis.⁴⁰

Table 3.5 provides a comparison of these membrane processes.

TABLE 3.5
Membrane Processes

<u>Process</u>	<u>Driving Force</u>	<u>Range (Micron)</u>
Electrodialysis	Electric Potential	E-2 to E-4
Dialysis	Concentration	E-1 to E-3
Reverse Osmosis	Pressure	E-2 to E-3

Electrodialysis (ELECD) has received limited application within the nuclear industry in the U.S.,⁴¹ the UK,⁴² and the USSR.²⁹ Reference 41 reports the preliminary development of several promising membranes for cesium separation. Researchers in the UK report effective and economical membrane separation of cesium in Low- and Medium-

Level Radwastes.⁴² Reference 29 reports successful volume reduction of LLW streams by ELECD prior to immobilization in bitumen or cement. The concept of a combined electro-dialysis-ion exchange (EIE) system is shown in Fig. 3.2.

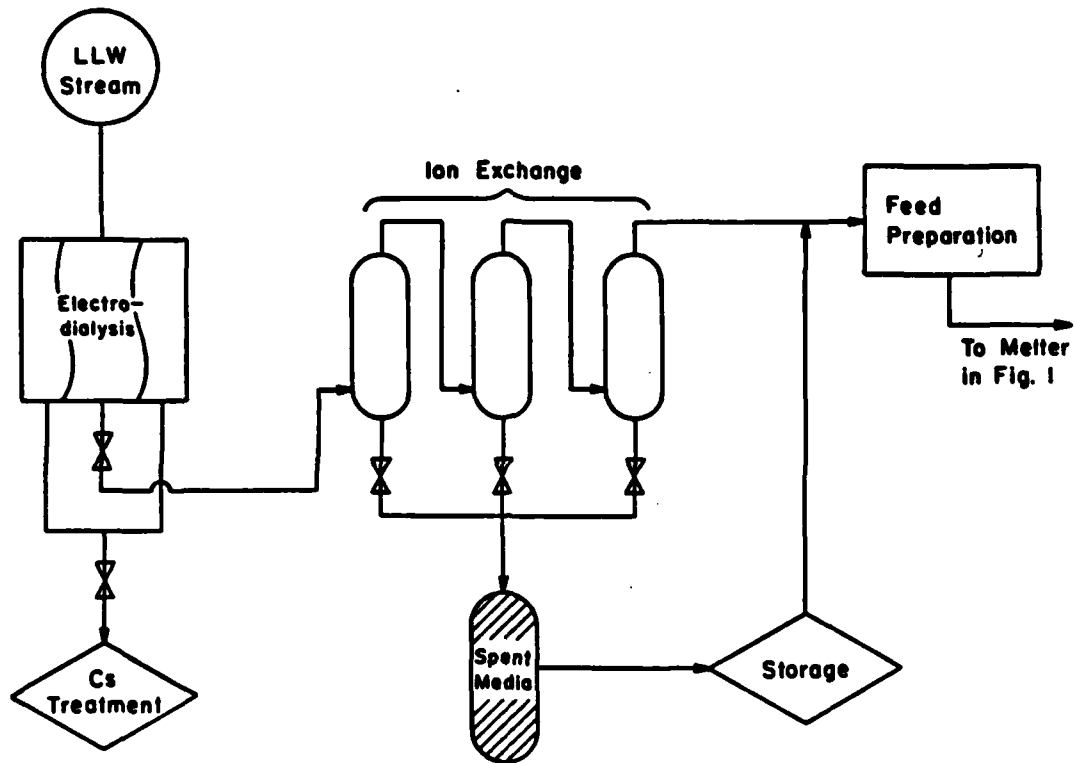


Fig. 3.2. Electro-dialysis-Ion Exchange PILLWV

ELECD has been shown to efficiently and economically separate cesium,⁴² but a follow-on immobilization process must be utilized to obtain a waste form acceptable for disposal. This follow-on treatment decreases in part the volume reduction capability of the process, but significant overall system effectiveness is attainable.⁴²

Cesium decontamination factors of 2000 for ELECD are reported.⁴² Table 3.6 summarizes the melter feed concentrations of an EIE. These values are calculated by the sequential use of the DF formula and the respective process DF's.

TABLE 3.6
EIE Melter Feed Cesium Concentration
(1000 MWe-yr)

	Initial Cs Conc ²⁰ (Ci/m ³)	ELECD ⁴² DF	ELECD Treated Cs Conc (Ci/m ³)	Ion Exchange ³⁴ DF	EIE Treated Cs Conc (Ci/m ³)
BWR LLW	8.640E-1	2000	4.320E-4	10000	4.320E-8
PWR LLW	4.074E-1	2000	2.037E-4	10000	2.037E-8

Comparison of the melter feed concentrations of Table 3.4 and 3.6 shows an improvement of 3 orders in magnitude for a proposed EIE process versus an ion exchange process.

In addition, Table 3.6 shows that ELECD can initially decrease the cesium concentration of the LLW stream fed to

ion exchange columns, which increases the life of the ion exchange media. ELECD alone effectively removes specific ions from LLW streams, however the requirement of a follow-on immobilization step for the concentrated waste stream is a significant disadvantage. Possible follow-on immobilization steps include ion exchange, chemical precipitation, or solidification in either a thermosetting resin or a DOW polymer. Reference 29 briefly indicates preliminary success in a combined electro dialysis-ion exchange technique in preparation for bituminization or cementation. This combined technique provides the desired cesium partitioning, however an effective immobilization technique for the partitioned cesium waste stream must be determined.

3.5 Conclusion

Of the three identified processes that selectively partition cesium from LLW streams, ion exchange is the preferred method. Ion exchange technology is well developed and may be easily integrated into the LLW process. Ion exchange media of high cesium selectivity in LLW streams and high cesium retention when vitrified are commercially available. Apparently, the effectiveness of chemical precipitation is questionable. In addition, the process is waste stream specific, and the thermal stability of the precipitate is to be determined. Electrodialysis has

potential, but its volume reduction capability is degraded by the follow-on immobilization techniques, and industrial development of the process is still to be completed.

CHAPTER 4

PILLWV REGULATORY COMPLIANCE AND COST ESTIMATION

4.1 Introduction

Any immobilized waste form must conform to all State and Federal regulatory requirements. These requirements set specific standards for stability, transportation, radiation protection, and final disposal of Radwaste. The Radwaste regulatory environment is very dynamic and is further complicated at the Federal level by the existence of four separate agencies with partially overlapping authority, i.e. the Environmental Protection Agency (EPA), the Nuclear Regulatory Commission (NRC), the Department of Transportation (DOT), and the Department of Energy (DOE). These agencies are autonomous and often issue conflicting regulatory requirements. Tables 4.1 and 4.2 show the applicable regulations and their interrelationships.

LLWV is an unconventional LLW immobilization method. Therefore, it must not only comply with the regulatory requirements and be technically superior to conventional methods, but it must also be cost competitive. Regulatory aspects and cost estimations of the PILLWV waste form will be discussed in turn.


TABLE 4.1
 Federal Regulations
 Applicable to Waste Management⁴³

<u>Regulation</u>	<u>Federal Agency</u>	<u>Title</u>
10 CFR 20	NRC	Standards for Protection Against Radiation
10 CFR 50	NRC	Policy Relating to the Siting of Fuel Reprocessing Plants and Related Waste Management Facilities
10 CFR 60	NRC	Disposal of High-Level Radioactive Wastes in Geologic Repositories
10 CFR 61	NRC	Licensing Requirements for Land Disposal of Radioactive Wastes
10 CFR 71	NRC	Packaging of Radioactive Material for Transport and Transportation of Radioactive Material Under Certain Conditions
40 CFR 61	EPA	Clean Air Act, Section 112
40 CFR 141	EPA	Drinking Water Regulations
40 CFR 190	EPA	Environmental Radiation Protection Standards
40 CFR 191 (DRAFT)	EPA	Environmental Standards for the Management and Disposal of Spent Nuclear Fuel, High-Level and Transuranic Radioactive Wastes

TABLE 4.1
(Continued)

40 CFR 192	EPA	Health and Environmental Protection Standards for Uranium and Thorium Mill Tailings
49 CFR 171-178	DOT	Requirements for Transportation of Radioactive Materials
Order 5480,XI	DOE	Standards and Requirements for Radiation Protection
Order 5820	DOE	Radioactive Waste Management

TABLE 4.2
Regulatory Interrelationships

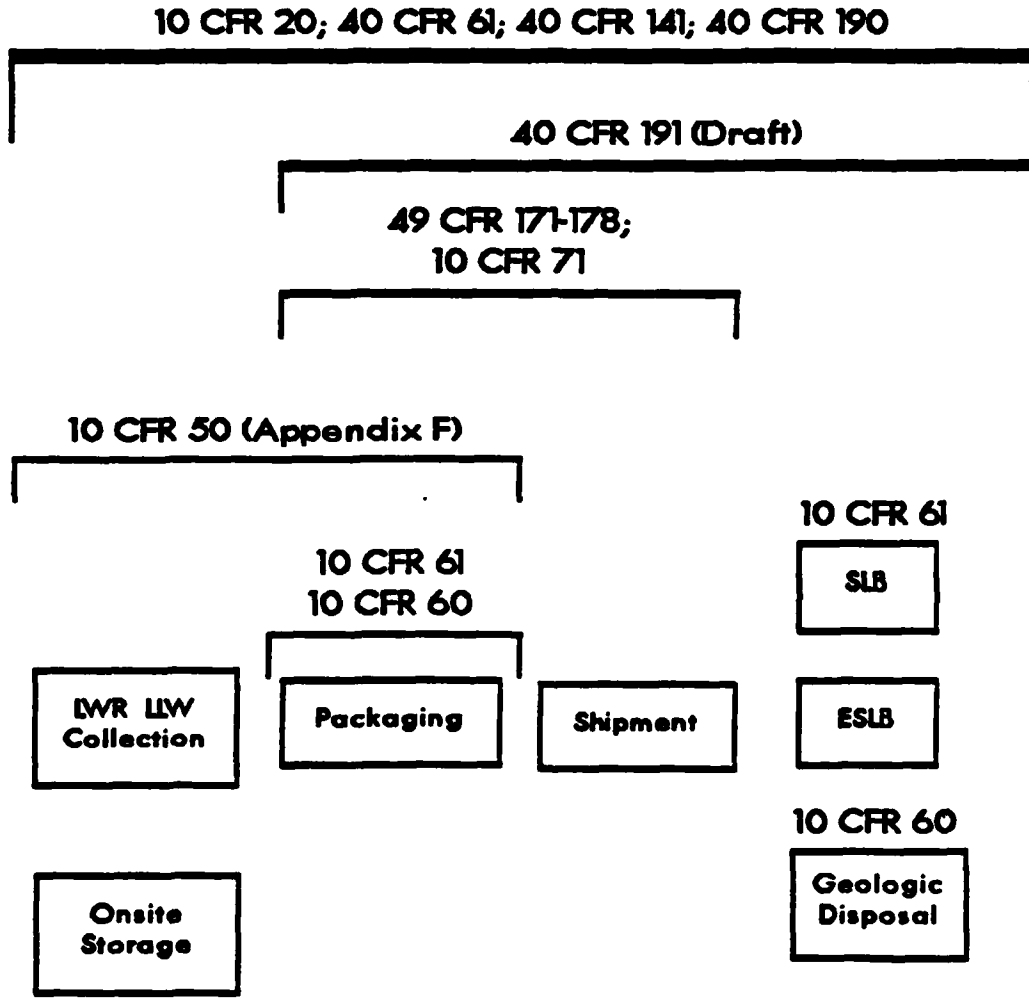

* Adapted from Ref. 43.

4.2 Regulatory Compliance

The glass of the reported LLWV process¹ meets all of the regulatory requirements for stability stated in 10 CFR 61 (Table 2.4) and for transport stated in 49 CFR 173 (Table 4.3). The PILLWV glass will also meet these regulatory requirements. In addition, Table 4.3 shows that the concentrated cesium PILLWV waste forms do not exceed Class C waste limits as defined in 10 CFR 61.

The methodology for LLW classification is provided in 10 CFR 61.55. The waste class, A, B, or C, is determined by comparing the specific activity of the waste for selected radionuclide(s) to the regulatory standards. Cesium has the most stringent overall standards of the selected radionuclides in 10 CFR 61 (Table 4.4).

In this work, cesium is selected for the determination of the vitrified waste product classification due to its impact on LLWV as described in chapter 2 and to the stringent classification previously discussed standards. A cesium dose rate to specific activity conversion factor for low level waste solid material is 1 rem/hr per 200 Ci/m³.⁴⁵ Conversion of the drummed product dose rates gives specific activities that may be compared to the regulatory standards (Table 4.5).

TABLE 4.3

Annual Vitrified Product 1100-MWe BWR^{1*}

Waste	Volume (m ³)	Activity (Ci)	Drummed Products			
			Number	mrem/hr	Shipping Container ⁺	Class
Resin	82	1,170	10.3	1.08	A	B
			31	10.8	B	B
			10.3	108	B	C
Conc liquid	226	362	38	0.095	Unshielded	A
			114	0.95	Shielded	B
			38	9.5	B	B
Filter Sludge	152	1,364	34	2.08	A	B
			102	20.8	B	B
			34	208	B	C

* Waste Classification in accordance with Federal Regulation 10 CFR 61 not included in Ref. 1.

⁺ Shipping Container Type in accordance with Federal Regulation 49 CFR 173. The dose limits of Ref. 1 are correctly shown as mrem/hr instead of rem/hr.

Table 4.4
Classification Standards for LLW⁴⁴

<u>Radionuclide</u>	<u>Class*</u>		
	<u>A</u>	<u>B</u>	<u>C</u>
All nuclides with half-life < 5 yrs	700	+	+
H-3	40	+	+
Co-60	700	+	+
Ni-63	3.5	70	700
Sr-90	0.04	150	7000
Cs-137	1	40	4600

* If the concentration (Ci/m³) < value given.
+ No limits set.

Table 4.5
Annual Vitrified Product Classification
1100-MWe BWR

<u>Waste</u> ¹	<u>Dose Rate</u> ¹ (mrem/hr)	<u>Calculated Activity</u> (Ci/M ³)	<u>Calculated Class</u>
Resin	1.08	0.22	A
	10.8	2.2	B
	108	21	B
Conc Liquid	0.095	0.019	A
	0.95	0.19	A
	9.5	1.9	B
Filter Sludge	2.08	0.42	A
	20.8	4.2	B
	208	42	C

The waste classifications of Table 4.3 are conservative adjustments of the calculated values of Table 4.4. These conservative adjustments are made to account for variance of cesium concentrations in individual waste streams, and for unusually high concentrations of the other regulated radionuclides.

4.3 Cost Estimation

Reference 1 gives an installation and operation cost comparison for LLW volume reduction techniques.

Vitrification was reported to be the cheapest volume reduction technique.¹ (Table 2.5)

Firm cost estimation figures for installation and operation of nuclear grade ion exchange systems are not available in the open literature, but an estimated 1984 annual installation and operation cost (AIOC) is \$108,000.

This cost was calculated in the following manner. The 1970 installation and yearly operation costs for an 800 gallon per minute, continuous, zeolite ion exchanger (to selectively remove cesium) are \$95,000 and \$11,100, respectively.⁴⁶ An annual equivalent installation cost

(AEIC) was calculated with the standard interest formula⁴⁷

$$AEIC = P * (A/P)_n^i ,$$

where

AEIC = Annual Equivalent Installation Cost

P = Present Value (\$95,000)

(A/P) = Capital Recovery Factor

i = Interest Rate

n = Number of Years

The assumed interest rate is 15% and the life expectancy of the zeolite ion exchanger of Ref. 46 is 10 years. The capital recovery factor, 0.19925, is determined from the tabulated data of Ref. 47. The AEIC is \$19,000.

This AEIC and the operation cost are evaluated in 1970 dollars, therefore a 1984 dollar adjustment is required for comparison with costs of Ref. 1. Producer price indexes are used for such adjustments. The 1970 and 1984 nonfood, excluding fuel, producer price indexes for manufacturing are 109.6 and 395.7, respectively.⁴⁸ The 1970 AEIC and operation cost are multiplied by the 1984 producer price index then divided by the 1970 index to give a 1984 estimated AEIC of \$108,000 and an operation cost of \$40,000. The AEIC and the operation cost are summed to give the AIOC (\$108,000). Table 4.6 shows that the Ion Exchange PILLWV is cost competitive with the LLWV system costs of Ref. 1.

TABLE 4.6

Ion Exchange PILLWV and LLWV Costs^{1a*}
(1984 \$1,000,000)

<u>Item</u>	<u>PILLWV</u>	<u>LLWV</u>
Total materials and burial	0.353	0.353
Solidification labor	0.037	0.037
VR operating costs	0.935	0.895
VR amortized capital cost	0.568	0.500
Drum credit	-0.090	-0.090
Transportation	<u>0.694</u>	<u>0.694</u>
Total	2.597	2.389

- ^a Case is for 1100-BWR, 1250 miles transportation, Barnwell, SC.
^{*} Ion Exchange PILLWV costs not included in Ref.1.

A 1986 installation cost of an ion exchange system that selectively removes cesium is \$71,000.⁴⁹ This figure shows that the 1984 estimated AEIC is very conservative, therefore an ion exchange LLWV system would appear to be even more attractive when compared to the installation cost of Ref.45. It is assumed that the 1986 installation cost reflects considerable technological and economic improvement in the process.

Table 4.7 summarizes the cost of volume reduction techniques of Table 2.5 and shows that the Ion Exchange PILLWV is cost competitive.

TABLE 4.7

Volume Reduction Cost Comparison¹⁺
(\$1,000,000)

<u>PROCESS</u>	<u>COST</u>
Vitrification	2.4
Vitrification with Ion Exchange *	2.6
Incineration/ Calcination	3.0
Evaporation	4.1
Incineration	4.7
Bituminization	5.5

⁺Costs are for a 1100-MWe BWR, 1250 miles transportation to Barnwell, S.C.

*Vitrification with Ion Exchange not Included in Ref.1. Incineration/calcination, evaporation, and incineration all use cementation as the immobilization technique.

Table 4.7 shows that the ion exchange PILLWV is cheaper than the traditional immobilization methods and the cost of the ion exchange improvement is only 4.5% of the LLWV cost of Ref. 1.

A comparison of the base disposal charges (cubic foot) is shown in Table 4.8.

TABLE 4.8

Comparison of Base Disposal Charges
 Barnwell, S. C.
 (1100-MWe BWR)

<u>Process</u>	<u>Volume (Ft³)</u>	<u>Total Charges (@ \$25.112/ft³)</u>
Vitrification	3000	\$75,000
Cementation	26000	\$650,000

This base disposal cost estimate is made by converting the total number of 55-gallon drums of PILLWV (Table 4.3) into cubic feet and multiplying this figure by the Barnwell standard waste charge of Table A-1. Cementation has a volume increase factor of 1.6.⁵⁰ The cementation cost estimate was calculated by multiplying the total waste volume (Table 4.3) by the volume increase factor and by the standard charge of Table A-1. Due to insufficient data, weight and curie surcharges are not included in this cost estimate.

4.4 Conclusion

The PILLWV waste form meets all regulatory standards for stability, transport, radiation protection, and disposal as LLW. The highest waste classification of the drummed products is class C. The volume reduction cost comparisons show that the PILLWV is cost competitive with the LLWV

process of Ref. 1. The basic cubic foot disposal charges for vitrification are 9 times cheaper than cementation.

CHAPTER 5

SUMMARY AND RECOMMENDATIONS FOR FURTHER STUDY

5.1 Summary of Results

The objective of this thesis, as stated in section 1.2 was to analyze the traditional LLW immobilization options, to review the impact of the LLW stream composition on LLWV, then to propose and discuss several techniques to control the volatile radionuclides in a Process Improved LLWV system (PILLWV).

The analysis, in chapter 2, showed several technological and cost disadvantages of the traditional LLW immobilization options. Cementation and bituminization have high cesium leachability and low waste loading in comparison with glass.¹³ The 300% escalation of SLB disposal fees dictates the use of an immobilization process which optimizes volume reduction. The LLWV process of Ref. 1 is also analyzed in chapter 2. Cesium is identified as the key volatile radionuclide to be controlled in order for vitrification to be a viable LLW immobilization option. The analysis shows cesium to be the predominant radionuclide in LLW streams,²⁰ to be the principal source term in LLWV DBA's,¹ and to be randomly sorbed/desorbed by the melter and offgas components during vitrification.²²

In chapter 3, an improvement to LLWV was proposed which relies on partitioning, and virtually eliminates the loss of

cesium from the LLWV process. Ion exchange is the preferred method of the three identified processes that selectively partition cesium from the LLWV stream. Ion exchange technology is fully developed and may be easily integrated into the vitrification process. In addition, ion exchange media of high cesium selectivity and high cesium retention when vitrified are commercially available. The other possible process improvements have serious technological obstacles which must be first studied, understood, and overcome before industrial applications may be considered. The major obstacles of chemical precipitation and electro dialysis include the questionable thermal stability of precipitates, process applicability to specific waste streams and selection of a follow-on immobilization process.

The following chapter showed that the PILLWV waste form complies with all regulatory standards for stability, transportation, and disposal as LLW. The highest waste classification of PILLWV process is class C. The volume reduction cost comparisons of chapter 4 show that the PILLWV is cost competitive with the LLWV process of Ref. 1. Finally, the standard disposal charges (cubic foot) for the vitrification waste forms are significantly lower than for the cementation waste forms.

High disposal costs and technical limitations of the traditional LLW immobilization techniques necessitated investigation of alternative methods. The PILLWV yields an

improved waste product and effectively controls cesium volatility which should facilitate the licensing procedure of a prospective LLWV facility. The comparison of the technical specifications, of the regulatory compliance, and of the cost considerations shows the PILLWV to be the superior immobilization option.

5.2 Recommendations for Future Study

Further work is recommended in the following areas:

(1) A design study, and pilot testing of the ion exchange PILLWV to verify the type of ion exchange column, and the optimum exchange media. In addition, the study should include an economic assessment of a large scale commercial LLW immobilization facility.

(2) An experimental investigation to determine the properties of the precipitates identified in chapter 3. The emphasis of the study should be on the thermal stability of the precipitates during vitrification, and the elimination of the process constraints imposed by specific waste streams.

(3) A design study and experimental test of an electrodialysis PILLWV to determine specific membrane (s), and the optimum follow-on immobilization technique.

(4) A design study, and experimental testing of the ion exchange PILLWV to produce partitioned radiation sources for medical, industrial, or institutional uses. The study should include media selection, and an economic assessment.

APPENDIX A
LLW DISPOSAL RATE SCHEDULES

The 1983 and 1985 commercial LLW disposal fees are shown in Table A1, Table A2, Table A3, and Table A4. Tables A1, A2, and A3 show the 1985 LLW disposal charges for the Barnwell Low-Level Radioactive Waste Disposal Facility, the Washington Nuclear Center, and the Nevada Nuclear Center, respectively. Table A4 provides the 1983 LLW disposal charges for each of these facilities.

TABLE A1
BARNWELL RATE SCHEDULES¹⁸
(DECEMBER 9, 1985)

1. BASE DISPOSAL CHARGES: (Not including Surcharges and Barnwell County Business License Tax)

A. Standard Waste	\$ 25.112/ft. ³
B. Biological Waste	\$ 26.112/ft. ³
C. Special Nuclear Material (SNM) plus \$1.75 per Gram SNM	\$ 25.112/ft. ³

Note: Minimum charge per shipment, excluding Surcharges and specific Other Charges is \$500.00

2. SURCHARGES:

A. Weight Surcharges (Crane Loads Only)

<u>Weight of Container</u>	<u>Surcharge Per Container</u>
0 - 1,000 lbs.	No Surcharge
1,001 - 5,000 lbs.	\$ 275.00
5,001 - 10,000 lbs.	\$ 550.00
10,001 - 20,000 lbs.	\$ 825.00
20,001 - 30,000 lbs.	\$1,100.00
30,001 - 40,000 lbs.	\$1,650.00
40,001 - 50,000 lbs.	\$2,200.00
greater than 50,000 lbs.	By Special Request

B. Curie Surcharges:

<u>Curie Content Per Shipment</u>	<u>Surcharge Per Shipment</u>
0 - 1	No Surcharge
1.1 - 5	\$ 1,500.00
5.1 - 15	\$ 2,250.00
15.1 - 25	\$ 3,000.00
25.1 - 50	\$ 4,500.00
50.1 - 75	\$ 5,500.00
75.1 - 100	\$ 7,450.00
100.1 - 150	\$ 8,900.00
150.1 - 250	\$12,000.00
250.1 - 500	\$15,000.00
500.1 - 1,000	\$18,000.00
1,000.1 - 5,000	\$24,000.00
Greater than 5,000	By Special Request

TABLE A1 (CONTINUED)

- C. Special Handling Surcharge may apply on unusually large or bulky containers. These type containers are acceptable upon approval of prior request.

3. OTHER CHARGES

- A. Cask Handling Fee \$600.00 per cask, minimum
- B. Taxes and Special Funds
1. Perpetuity Escrow Fund \$ 2.80 per ft.³
 2. South Carolina Low Level Radioactive Waste Disposal Tax \$ 4.00 per ft.³
 3. Southeast Regional Compact Fee 46.2¢ per ft.³
 4. Barnwell County Business License Tax:

A 2.4% Barnwell County Business License Tax shall be added to the Total of all disposal fees.

NOTE: Items 3.B. 1, 2, and 3 are included in Item 1, Base Disposal Charges.

TABLE A2

NEVADA NUCLEAR CENTER RATE SCHEDULE¹⁸
(DECEMBER 9, 1985)

1. DISPOSAL CHARGES

A. SOLID MATERIAL

Steel Drums, Wood Boxes:

<u>R/HR AT CONTAINER SURFACE</u>	<u>PRICE PER CU. FT.</u>
0.00 - 0.20	\$ 20.61
0.201 - 1.00	22.34
1.01 - 2.00	25.09
2.01 - 5.00	30.02
5.01 - 10.00	35.43
10.01 - 20.00	45.82
20.01 - 40.00	56.77
40.01 - 60.00	86.29
60.01 - 80.00	103.55
80.01 - 100.00	114.19
Over 100.00	By Request

Disposal Liners Removed from Shield: (Greater than 12.0 cu.ft. each)

<u>R/HR AT CONTAINER SURFACE</u>	<u>SURCHARGE PER LINER</u>	<u>PRICE PER CU. FT.</u>
0.00 - 0.20	No Charge	\$ 20.61
0.201 - 1.00	\$ 271.72	20.61
1.01 - 2.00	668.54	20.61
2.01 - 5.00	940.98	20.61
5.01 - 10.00	1,360.17	20.61
10.01 - 20.00	1,735.76	20.61
20.01 - 40.00	2,156.95	20.61
40.01 - 60.00	2,557.19	20.61
60.01 - 80.00	2,951.60	20.61
80.01 - 100.00	3,351.84	20.61
Over 100.00	By Request	By Request

B. Biological Waste, Animal Carcasses \$22.37/cu.ft.

TABLE A2
(CONTINUED)

2. SURCHARGE FOR HEAVY OBJECTS:	
Less than 10,000 pounds	No Charge
10,001 pounds to Capacity of Site Equipment	\$214.00 plus \$.10 per lb. above 10,000 lbs.
3. SURCHARGE FOR CURIES (Per Load):	
Less than 100 curies	No Charge
101 - 300 curies	\$1,554.00 plus 20¢/Ci above 100 Ci.
301 - License Limits	By Request
4. MINIMUM CHARGE PER SHIPMENT	\$483.00
5. CASK HANDLING FEE:	\$794.00 minimum each
6. WASTE CONTAINING CHELATING AGENTS IN PACKAGES AMOUNT GREATER THAN 1% BY WEIGHT:	By Request
7. SURCHARGE FOR NON-ROUTINE MAN-REM EXPOSURE (DUE TO DESIGN OR PHYSICAL DEFECT OF CONTAINER OR SHIELD):	\$29.21 per man millirem
8. DECONTAMINATION SERVICES (If Required)	\$106.20 per man hour plus supplies at cost plus 15%
9. CONTAINER VOLUMES:	
55 Gallon Drums - 7.50 cu. ft.	
30 Gallon Drums - 4.01 cu. ft.	
5 Gallon Drums - 0.67 cu. ft.	

TABLE A3

WASHINGTON NUCLEAR CENTER RATE SCHEDULE¹⁸
(DECEMBER 9, 1985)

1. DISPOSAL CHARGES

A. SOLID MATERIAL

Steel Drums, Wood Boxes:

<u>R/HR AT CONTAINER SURFACE</u>		<u>PRICE PER CU. FT.</u>
0.00	- 0.20	\$ 24.90
0.201	- 1.00	26.76
1.01	- 2.00	29.66
2.01	- 5.00	31.00
5.01	- 10.00	36.08
10.01	- 20.00	45.99
20.01	- 40.00	56.34
40.01	- 60.00	80.24
60.01	- 80.00	95.75
80.01	- 100.00	105.37

Disposal Liners Removed from Shield: (Greater than 12.0 cu. ft. each)

<u>R/HR AT CONTAINER SURFACE</u>	<u>SURCHARGE PER LINER</u>	<u>PRICE PER CU. FT.</u>
0.00	- 0.20	No Charge \$24.90
0.201	- 1.00	\$ 258.46 24.90
1.01	- 2.00	634.84 24.90
2.01	- 5.00	890.80 24.90
5.01	- 10.00	1,288.52 24.90
10.01	- 20.00	1,644.84 24.90
20.01	- 40.00	2,042.57 24.90
40.01	- 60.00	2,422.73 24.90
60.01	- 80.00	2,795.36 24.90
80.01	- 100.00	3,175.52 24.90

B. LIQUID WASTES

1. Aqueous liquids in vials, less than 50 ml. each \$31.84/cu.ft.
2. Aqueous liquids, absorbed 24.90/cu.ft.

C. BIOLOGICAL WASTE, ANIMAL CARCASSES 26.76/cu.ft.

TABLE A3
(CONTINUED)

2.	SURCHARGE FOR HEAVY OBJECTS:	
	Less than 10,000 pounds	No Charge
	10,000 pounds to Capacity of Site Equipment	\$194.29 plus 10¢ per lb. above 10,000 lbs.
3.	SURCHARGE FOR CURIES (Per Load)	
	Less than 100 curies	No Charge
	100 - 300 curies	\$1,414.46 plus 19¢/Ci above 100 Ci
	301 - License Limits	By Request
4.	SURCHARGE FOR SPECIAL NUCLEAR MATERIAL (SNM)	\$2.55 per gram of Special Nuclear Material by Isotope Weight
5.	MINIMUM CHARGE PER SHIPMENT	\$435.00
6.	CASK HANDLING FEE:	\$718.00 minimum each
7.	WASTE CONTAINING CHELATING AGENTS IN PACKAGES AMOUNT GREATER THAN 1% BY WEIGHT:	By Request
8.	SURCHARGE FOR NON-ROUTINE MAN-REM EXPOSURE (DUE TO DESIGN OR PHYSICAL DEFECT OF CONTAINER OR SHIELD)	\$26.67 per man millirem
9.	DECONTAMINATION SERVICES (If Required)	\$96.92 per man hour plus supplies at cost plus 21%
10.	CONTAINER VOLUMES:	
	55 Gallon Drums - 7.50 cu. ft.	
	30 Gallon Drums - 4.01 cu. ft.	
	5 Gallon Drums - 0.67 cu. ft.	

TABLE A4
(CONTINUED)

Facility: Surcharges (effective):	Barnwell Low-Level Radioactive Waste Disposal Facility ^a		Washington Nuclear Center ^b		Nevada Nuclear Center ^d		
	Curie content (Ci)	Surcharge/shipment (\$/shipment)	<100 Ci 100-300 Ci	>300 Ci	<100 Ci 100-300 Ci	>300 Ci	No charge \$1,200 + 15¢/Ci above 100 Ci
	0-1	0.00					By request
	1-5	500					
	5-15	750					
	15-25	1,000					
	25-50	1,500					
	50-75	2,000					
	75-100	2,500					
	100-150	3,000					
	150-250	4,000					
	250-500	5,000					
	500-1000	6,000					
	1000-5000	8,000					
	>5000	Special request					
Biological slimes (\$/m ³):	25		52		48		
Liquid wastes (\$/m ³):			In vials <50 mL also Scintillation liquids adsorbed	192	Scintillation liquids adsorbed	178	
			Aqueous liquids adsorbed	192			
			<10,000 lb - no charge	0.0	<10,000 lb - no charge		
			>10,000 lb to equipment trailer \$176.00 + 9¢/lb above 10,000 lb wt		>10,000 lb to equipment trailer \$165.00 + 9¢/lb above 10,000 lb wt		
Weight surcharges:	Weight (10 ³ lb)	Surcharge (\$/container)					
	0-1	None					
	1-5	250					
	5-10	500					
	10-20	750					
	20-30	1,000					
	30-40	1,500					
	40-50	2,000					
	>50	Special request					

^aIn addition to listed charges, there are a variety of minimum fees and special charges. Data taken from rate schedule provided by burial ground operators. Certain sites will not accept certain types of LIL or accept only under special permit.

^bOperated by Chem Nuclear Service Inc. In addition to the charges shown, there is a 2.42 Barnwell Co. business tax on the total of all fees. There is a surcharge of \$17.00/m³ for drummed radioactive waste weighing less than 400 lb per drum and NOT shipped palletized in an open-top van, or a flat bed trailer.

^cOperated by U.S. Ecology. Surcharge for special nuclear materials (SNM) of \$2.50/gram of special nuclear material by isotopic weight.

^dOperated by U.S. Ecology.

^eIncludes State of South Carolina \$79.45/m³ perpetual encrow land charge.

^fIncludes State of Washington fees: \$61.00/m³ for perpetual case and maintenance, \$0.03/m³ site closure fund and \$10.59/m³ radioactive waste surveillance surcharge.

^gThird-party inspection required at the shipper expense.


Appendix B

LWR WASTE STREAM CHARACTERISTICS

Tables B1 and Table B2 show the the LLW stream characteristics for both BWR's and PWR's.

TABLE B1
BWR WASTE STREAM CHARACTERISTICS²⁰

ORNL DWG 83-494R2

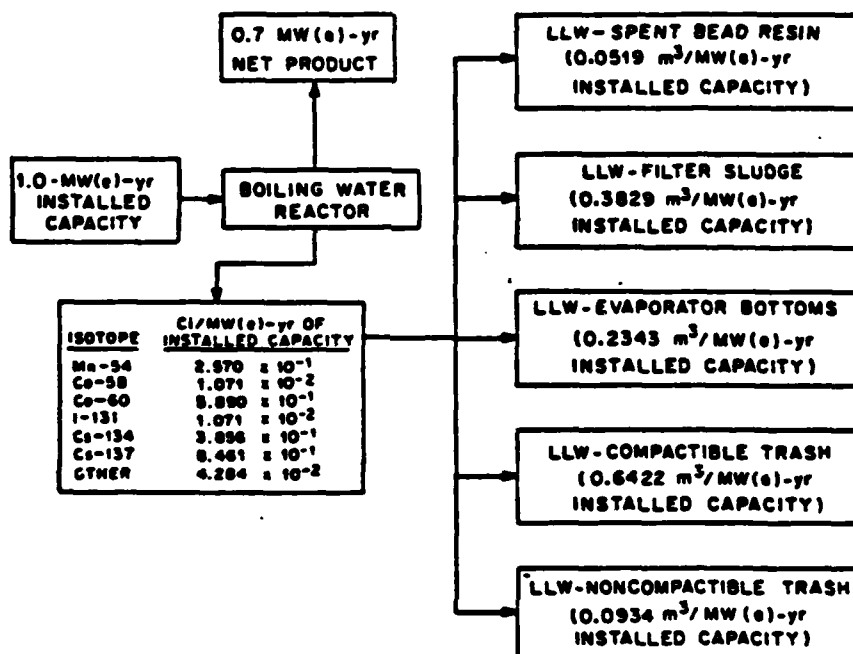


Fractions of elements from BWRs to waste streams

Element	Waste streams (LLW)				
	Spent resin	Filter sludge	Evaporator bottoms	Compactible trash	Noncompactible trash
Manganese	2.6354 × 10 ⁻²	9.3917 × 10 ⁻¹	3.1183 × 10 ⁻²	2.2344 × 10 ⁻³	1.0599 × 10 ⁻³
Cobalt	7.0285 × 10 ⁻²	8.7092 × 10 ⁻¹	3.6058 × 10 ⁻²	1.8339 × 10 ⁻³	8.7941 × 10 ⁻⁴
Cesium	7.5028 × 10 ⁻¹	1.6043 × 10 ⁻¹	8.8776 × 10 ⁻²	3.4986 × 10 ⁻⁴	1.6596 × 10 ⁻⁴
Other	4.1677 × 10 ⁻²	1.3814 × 10 ⁻¹	8.1222 × 10 ⁻¹	3.4061 × 10 ⁻³	2.5635 × 10 ⁻³

TABLE B2
PWR WASTE STREAM CHARACTERISTICS²⁰

ORNL DWG 83-493R2

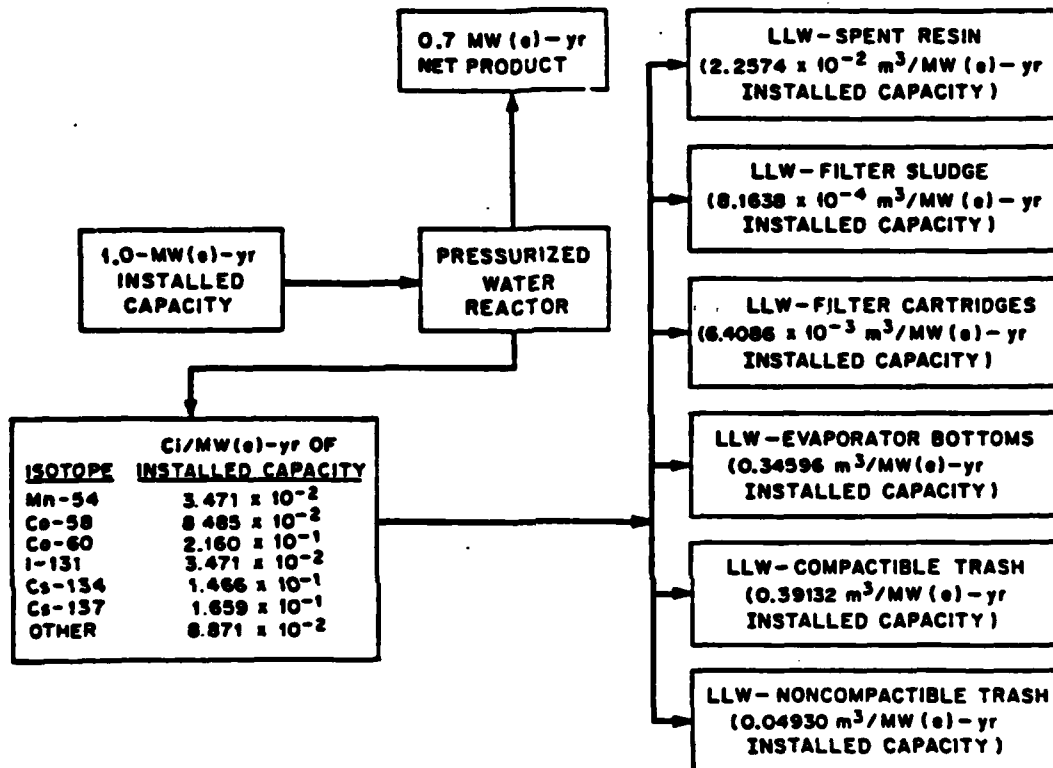

Fractions of elements from PWRs to waste streams

Element	Waste stream (LLW)					
	Spent resin	Filter sludge	Filter cartridges	Evaporator bottoms	Compactible trash	Noncompactible trash
Manganese	6.2464×10^{-1}	1.3035×10^{-2}	3.3891×10^{-1}	2.0335×10^{-2}	2.0202×10^{-1}	1.0367×10^{-1}
Cobalt	4.8884×10^{-1}	1.8298×10^{-2}	4.7574×10^{-1}	7.5118×10^{-1}	6.3433×10^{-1}	3.2551×10^{-1}
Cesium	9.0264×10^{-1}	3.1939×10^{-1}	8.3041×10^{-2}	4.8848×10^{-1}	4.1249×10^{-1}	2.1167×10^{-1}
Other	4.3348×10^{-1}	1.3360×10^{-1}	3.4735×10^{-2}	4.8484×10^{-1}	1.6922×10^{-2}	8.6837×10^{-1}

REFERENCES

1. D.E. Larson et al. Assessment of Power Reactor Waste Immobilization by Vitrification, EPRI-3225, Electric Power Research Institute, Palo Alto, California, (1983).
2. W.S. Horton and A.M. Ougouag, "Low-Level Radioactive Waste Vitrification: the Effect of Cs Partitioning," presented at Waste Management '86, Tucson, Arizona, March, 1986, to be published in the Conference Proceedings, (1986).
3. Radioactive Waste Management, U.S. Department of Energy, DOE ORDER 5820.2, p.4, Washington, D.C., (1984).
4. Disposal of High-Level Radioactive Wastes in Geologic Repositories, U.S. Nuclear Regulatory Commission, Code of Federal Regulations, Title 10, Part 60.
5. Donald C. Stewart, Data for Radioactive Waste Management and Nuclear Applications, John Wiley & Sons, New York, New York, p. 141, (1985).
6. Radioactive Waste Management, U.S. Department of Energy, DOE ORDER 5820.2, p.5, Washington, D.C., (1984).
7. Disposal of High-Level Radioactive Wastes in Geologic Repositories, U.S. Nuclear Regulatory Commission, Code of Federal Regulations, Title 10, Part 60.
8. *ibid.*
9. Licensing Requirements For Land Disposal of Radioactive Waste, U.S. Nuclear Regulatory Commission, Code of Federal Regulations, Title 10, Part 61.
10. Disposal of High-Level Radioactive Wastes in Geologic Repositories, U.S. Nuclear Regulatory Commission, Code of Federal Regulations, Title 10, Part 60.
11. R. A. Shaw et al., "LLW Disposal Technology: Classification and Coordination," presented at Waste Management '86, Tucson, Arizona, March 1986, to be published in the Conference Proceedings, (1986).
12. H. Cember, Introduction to Health Physics, Second Edition-Revised and Enlarged, p. 340, Pergamon Press, New York, New York, (1983).

13. J. M. Rusin et al., "Alternate Waste Forms --A Comparative Study," Scientific Basis for Nuclear Waste Management, 2, p.255, Plenum Press, New York, New York, (1980).
14. Rustum Roy, Radioactive Waste Disposal, Vol 1: The Waste Package, p.23, Pergamon Press, New York, New York, (1982).
15. J. E. Mendel et al., A State of the Art Review of Materials Properties of Nuclear Waste Forms, PNL-3802, Pacific Northwest Laboratory, Richland, Washington, (1981).
16. J.R. Wiley, "Decontamination of Alkaline Radioactive Wastes by Ion Exchange," Ind. Eng. Chem. Process Des. Dev., 17, No.1, p.67, American Chemical Society, Washington D.C., (1978).
17. J. Arod, "Bituminization of Radioactive Wastes: Safety Studies," Nuclear and Chemical Waste Management, 3, p.179, Pergamon Press, New York, New York, (1982).
18. D. Ebenhack, Chem Nuclear Systems, Inc., Columbia, South Carolina, personal communication, November, (1985).
19. Spent Fuel and Radioactive Waste Inventories, Projections, and Characteristics, DOE/RW-0006, Rev. 1, U.S. Department of Energy, p. 246, Washington, D.C., (1983).
20. C. Forsberg, W. Carter, and A. Kibbley, Flowsheets and Source Terms for Radioactive Waste Projections, ORNL/TM-8462, p. 78, Oak Ridge National Laboratory, Oak Ridge, Tennessee, (1985).
21. J. Phillips et al., A Waste Inventory Report for Reactor and Fuel Fabrication Facility Wastes, ONWI-20 NUS-3314, p. 243, NUS Corporation, Gaithersberg, Maryland, (1979).
22. L. Klinger and K. Armstrong, An Evaluation of Operating Experience for Low-Level Nuclear Waste Processing, MLM-3229, pp. 55-59, Mound, Miamisburg, Ohio, (1985).
23. G.M. Hughes et al., "Conceptual Design of High-Level Waste Vitrification Process at West Valley Using a Slurry-Fed Ceramic Melter," Advances in Ceramics, 8, p.143, American Ceramics Society, Columbus, Ohio, (1984).
24. P.K. Baumgarten et al., "Development of an Ion-Exchange Process for Removing Cesium from High-Level Radioactive Liquid Wastes," Scientific Basis for Nuclear Waste Management, 2, p.875, Plenum, New York, New York, (1980).

25. C.A. Langton et al., "Cement-Based Waste Forms for Disposal of Savannah River Plant Low-Level Radioactive Salt Waste," Mat. Res. Soc. Proc., 26, p.575, North-Holland, New York, New York, (1984).
26. Treatment of Low- and Intermediate-level Liquid Radioactive Wastes, Technical Reports Series No. 236, p. 172, IAEA, Vienna, Austria, (1984).
27. S. Forsberg et al., "Fixation of Medium-Level Wastes in Titanates and Zeolites: Progress Towards a System for Transfer of Nuclear Reactor Activities From Spent Organic to Organic Ion Exchangers," Scientific Basis for Nuclear Waste Management, 2, p.867, Plenum Press, New York, New York, (1980).
28. F. Kawamura and K. Motojima, "Using Copper Hexacyano-Ferrate (II) Impregnated Zeolite for Cesium Removal from Radioactive Waste," Nuc. Tech., 58, p.242, ANS, La Grange Park, Illinois, (1982).
29. F.V. Rauzen et al., "Ion Exchange and Electrodialysis in Liquid Radioactive-Waste Decontamination," Atomnaya Energiya, translated in Soviet Atomic Energy, 54, No. 6, p.705, Plenum Press, New York, New York, (1983).
30. B.E. Ryabchikov et al., "Treating Radioactive Waters with a Mixed Ion-Exchange Bed in a Continuous-Operation Plant," Atomnaya Energiya, translated in Soviet Atomic Energy, 55, No. 6, p.815, Plenum Press, New York, New York, (1984).
31. A.S. Nikiforov, et al., "Handling Radioactive Wastes from Nuclear Power Plants and Reprocessing Spent Nuclear Fuel," Atomnaya Energiya, translated in Soviet Atomic Energy, 50, No.2, p.116, Plenum Press, New York, New York, (1981).
32. C. Dallman, "Four Years Operating Experience with Graver's CI Process," The International Water Conference Thirty-Second Annual Meeting, p.113, Engineer's Society of Western Pennsylvania, Pittsburgh, Pennsylvania, (1971).
33. P.K. Baumgarten et al., "Ion Exchange Processes for Decontaminating Alkaline Radioactive Wastes," Waste Management '81, 2, p.1057, ANS, New York, New York, (1981).
34. D.K. Ploetz et al., "Conceptual Design of a Process for Removing Radioactivity from a Salt Solution," Advances in Ceramics Nuclear Waste Management, 8, p.183, American Ceramics Society, Columbus, Ohio, (1984).

35. S. Komarneni and R Roy, "Use of γ -Zirconium Phosphate for Cs Removal from Radioactive Wastes," Nature, 299, p.707, Macmillian Journals, London, United Kingdom, (1982).
36. S. Komarneni and R.Roy, " γ -Zirconium Phosphate as a Cs-Waste Form Form for Partitioned Wastes," Mat. Res. Soc. Symp. Proc., 15, p.77, North-Holland, New York, New York, (1983).
37. Radiological Health Handbook, U.S. Department of Health, Education, and Welfare, Bureau of Radiological Health, p.33, Rockville, Maryland, (1970).
38. Barbara A. Hacker and R.M. Wallace, Savannah River Laboratory, Aiken, South Carolina, personal communication, (1986).
39. D. K. Ploetz, West Valley Nuclear Services Co., Inc., West Valley, New York, personal communication, (1985).
40. Tom D. Reynolds, Unit Operations and Processes in Environmental Engineering, Brooks/Cole Engineering Division, Monterey, California, pp.235-240, (1982).
41. R.C. Roberts and M.K. Williams, Development of Low-Level Waste Treatment Systems: April-September 1982, MLM-3014, pp. 5-19, Mound, Miamisburg, Ohio, (1982).
42. A.D. Turner and R.M. Dell, "Electrochemistry and Radioactive Wastes," Atom, 327, p.14, Macmillian Journals, London, United Kingdom, (1984).
43. L.E. Trevorow, et al., Compatibility of Technologies with Regulations in the Waste Management of H-3, I-129, C-14, and Kr-85, Part II. Analysis, ANL-83-57, Argone National Laboratory, pp. 12-15, Argone, Illinois, (1983).
44. Licensing Requirements For Land Disposal of Radioactive Waste, U.S. Nuclear Regulatory Commission, Code of Federal Regulations, Title 10, Part 61.
45. Charles W. Mallory, "Regulatory Impacts on Radioactive Waste Transportation," Transactions of the American Nuclear Society, 41, Supplement #1, p.4, ANS, La Grange Park, Illinois, (1982).
46. C. Dallman, "Four Years Operating Experience with Graver's CI Process," The International Water Conference Thirty-Second Annual Meeting, p.113, Engineer's Society of Western Pennsylvania, Pittsburgh, Pennsylvania, (1971).

47. G.W.,Smith, Engineering Economy: Analysis of Capital Expenditures, 3rd Edition, p. 42 & 558, Iowa State Univ. Press, Ames, Iowa, (1979).

48. U. S. Bureau of the Census, Statistical Abstract of the United States: 1985 (105th Edition), p.469, Washington, D.C., (1984).

49. D.F. Malauskas, Commonwealth Edison, Chicago, Illinois, personal communication, (1986).

50. Low-Level Radioactive Waste Management Handbook Series, DOE/LLW-13Tc, p.92, EG&G Idaho, Idaho Falls, Idaho, (1984).

VITA

Walter S. Horton was born in Rock Hill, South Carolina on January 15, 1951. He received a B.S. in Chemistry from Clemson University in 1973. Prior to graduating from Clemson, he graduated from the U.S Army Airborne School and the U.S. Army Ranger School as a distinguished graduate in 1972. He was commissioned a Regular Army, Second Lieutenant in 1973. He is also a graduate of the following service schools: Armor Officer Basic Course, 1973; Infantry Mortar Platoon Leaders Course, 1973; Armor Officer Advanced Course, 1978; Command and General Staff College, 1985-- honor graduate. His most noteworthy military decorations include the Meritorious Service Medal, the Army Commendation Medal, and the Army Commendation Medal First Oak Leaf Cluster. His civilian honors include Outstanding First Year Lion in 1982 and Outstanding Young Man of America in 1983. He has co-authored the following publications:

Thomas H. Cook and Walter S. Horton, "Ammonium Chloride Control in Galvanizing Preflux," in Metal Finishing, Vol. 80, No. 8, p.19, Metals and Plastics Publications, Inc., Hackensack, NJ, 1982.

T. H. Cook, J. R. Thomasson, and W. S. Horton, "Selection and Use of Pickling Acid Inhibitors," in Metal Finishing, Vol. 80, No. 10, p.15, Metals and Plastics Publications, Inc., Hackensack, NJ, 1982.

W. S. Horton and A. M. Ougouag, "Low-Level Radioactive Waste Vitrification: the Effect of Cs Partitioning," presented at Waste Management '86, Tucson, Arizona, March, 1986, to be published in the Conference Proceedings, 1986.

END

DTIC

9-86